

University of Groningen

Solid state stabilization of proteins by sugars

Mensink, Maarten

IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.

Document Version

Publisher's PDF, also known as Version of record

Publication date:

2017

[Link to publication in University of Groningen/UMCG research database](#)

Citation for published version (APA):

Mensink, M. (2017). *Solid state stabilization of proteins by sugars: Why size and flexibility matter*. [Thesis fully internal (DIV), University of Groningen]. Rijksuniversiteit Groningen.

Copyright

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

Take-down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.

Inulin, a flexible
oligosaccharide I:
Review of its
physicochemical
characteristics

3

Carbohydrate Polymers 2015, volume 130, pages 405-419

Maarten A. Mensink, Henderik W. Frijlink,
Kees van der Voort Maarschalk, Wouter L.J. Hinrichs

ABSTRACT

Inulin, a fructan-type polysaccharide, consists of (2→1) linked β-D-fructosyl residues (n=2-60), usually with an (1↔2) α-D-glucose end group. The applications of inulin and its hydrolyzed form oligofructose (n=2-10) are diverse. It is widely used in food industry to modify texture, replace fat or as low-calorie sweetener. Additionally, it has several applications in other fields like the pharmaceutical arena. Most notably it is used as a diagnostic agent for kidney function and as a protein stabilizer. This work reviews the physicochemical characteristics of inulin that make it such a versatile substance. Topics that are addressed include morphology (crystal morphology, crystal structure, structure in solution); solubility; rheology (viscosity, hydrodynamic shape, gelling); thermal characteristics and physical stability (glass transition temperature, vapor sorption, melting temperature) and chemical stability. When using inulin, the degree of polymerization and processing history should be taken into account, as they have a large impact on physicochemical behavior of inulin.

INTRODUCTION

Inulin was discovered over two centuries ago by Rose¹ and since then its presence in many plants became apparent.² Some examples of plants containing large quantities of inulin are Jerusalem artichoke, chicory root, garlic, asparagus root, salisfy and dandelion root.³ More commonly consumed vegetables and fruits containing inulin are onion, leek, garlic, banana, wheat, rye and barley. Daily intakes have been estimated to range from 1 to 10 g per day in the Western diet.^{4,5} The average American diet contained between 1.3 and 3.5 g of inulin per day, with an average of 2.6 g.⁵ The European consumption of inulin appears to be substantially higher at 3 to 11 g per day, which is below reported tolerances of at least 10 to 20 g per day.^{6,7} Inulin has also been used safely in infant nutrition.⁸ This has led to the American Food and Drug Administration to issuing a Generally Recognized As Safe notification for inulin in 1992.⁹ Inulin is also used pharmaceutically, most notably as a diagnostic agent for the determination of kidney function.^{10,11}

Over the past decades, a lot of research has been done showing that inulin is a versatile substance with numerous promising applications. Several reviews have been published on inulin, its characteristics and functionality in food and pharma.¹²⁻¹⁶ This review aims to provide an overview of the relevant physicochemical properties of inulin, which make it such a useful excipient in food and pharma.

CHEMICAL STRUCTURE

Inulin, depending on its chain length, is classified as either an oligo- or polysaccharide and it belongs to the fructan carbohydrate subgroup. It is composed of β -D-fructosyl subgroups linked together by beta (2 \rightarrow 1) glycosidic bonds and the molecule usually ends with a (1 \leftrightarrow 2) bonded α -D-glucosyl group.^{12,17} The length of these fructose chains varies and ranges from 2 to 60 monomers. Inulin containing maximally 10 fructose units is also referred to as oligofructose.¹⁸ In food, oligofructose is more commonly used a sweet-replacer and longer chain inulin is used mostly as a fat replacer and texture modifier.¹² Both inulin and oligofructose are used as dietary fiber and prebiotics in functional foods. Its longer chain length makes inulin more useful pharmaceutically than oligofructose.

Before processing, the degree of polymerization of inulin depends on the plant source, time of harvest, and the duration and conditions of post-harvest storage.^{9,19,20} Processing itself also has a great influence on degree of polymerization of the obtained product as will be discussed in the section *Isolation and production*. Table 3.1 provides an overview of the structure and size of some carbohydrates frequently used in the pharmaceutical arena. The structures of a selection of those carbohydrates are shown in figure 3.1.

Like many oligosaccharides, inulin is heterodisperse. High performance anion exchange chromatography (HPAEC) with pulsed amperometric detection can be used to determine

the number average DP (DP_n) and the weight average DP (DP_w) of inulin.³⁶ Several chromatographic methods have been described, but HPAEC has a superior sensitivity and resolution.^{30,36} The ratio between DP_w and DP_n is a measure of the molecular weight distribution (polydispersity) of a sample. The DP and polydispersity of an oligo- or polysaccharide influence the physicochemical properties to a large extent.^{37,38}

Inulin is a unique oligo- or polysaccharide because its backbone does not incorporate any sugar ring, which can be seen in figure 3.1. The backbone is in essence polyethylene oxide.³⁰ This translates into a greater freedom to move and thus more flexibility of the molecule. Furthermore, inulin is built up mostly from furanose groups, which are more flexible than pyranose rings.^{2,32}

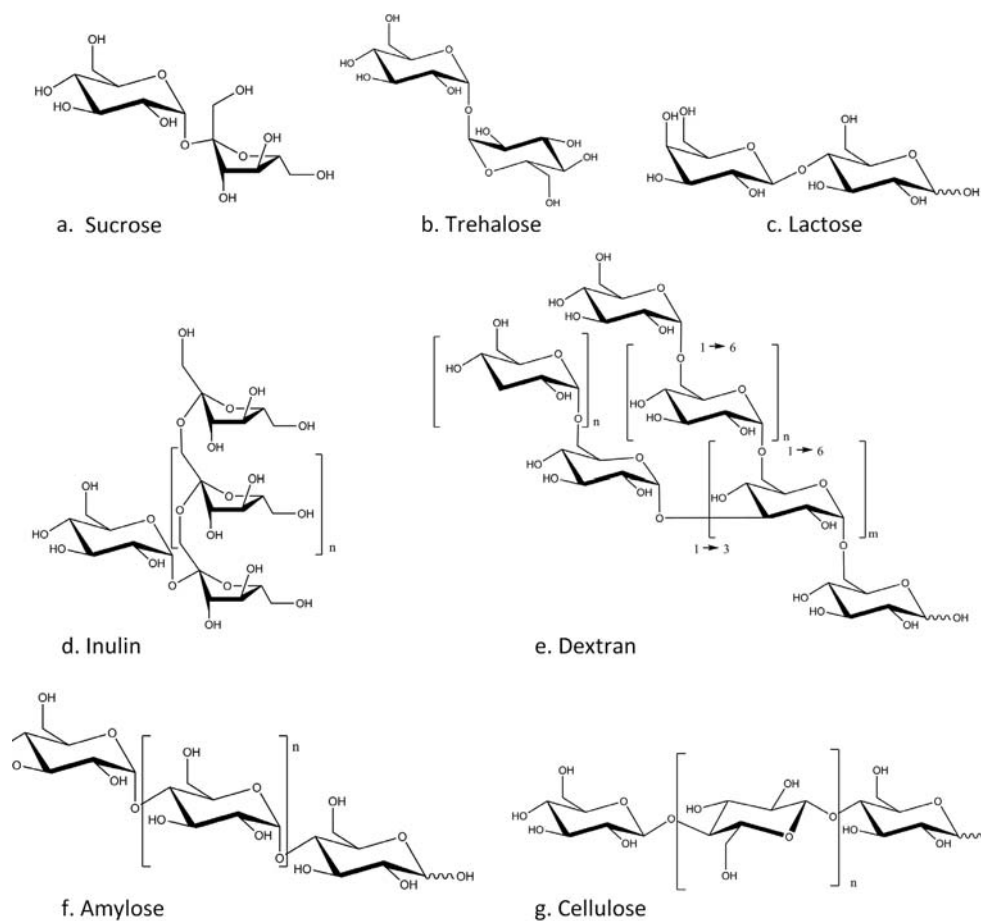


Figure 3.1 Chemical structures from a selection of the carbohydrates listed in table 3.1.

Table 3.1 Structure and size of some carbohydrates frequently used in food and pharma.

Carbohydrate	Building blocks & Linkages	Molecular weight (Da)	Backbone	Article cited
Glucose	α DGlc	1.8×10^2	-	22
D (+) Trehalose	α DGlc $p(1 \leftrightarrow 1)\alpha$ DGlc p	3.4×10^2	Linear	22,23
Sucrose	α DGlc $p(1 \leftrightarrow 2)\beta$ DFruf	3.4×10^2	Linear	22
β (+) Lactose	β DGal $p(1 \rightarrow 4)$ DGlc p	3.4×10^2	Linear	22
Maltodextrin	[4]- α DGlc $p(1 \rightarrow)_n$	1.8×10^2 to 3.2×10^3	Linear	24
Amylose (α -Glucan)	[4]- α DGlc $p(1 \rightarrow)_n$	5×10^5 to 2×10^6	Linear	22,25,26
Dextran (α -Glucan)	[6]- α DGlc $p(1 \rightarrow)_n$ (Main) α DGlc $p(1 \rightarrow 3)\alpha$ DGlc p (also $1 \rightarrow 2$) and $1 \rightarrow 4$) (Branches)	1.0×10^3 to $\sim 10^7$	Branched	22,27,28
Cellulose (β -Glucan)	[4]- β DGlc $p(1 \rightarrow)_n$	3×10^5 to 2×10^6	Linear	29
Inulin (Fructan)	[1]- β DFruf $(2 \rightarrow)_n$ (Main) α DGlc $p(1 \leftrightarrow 2)$ β DFruf (End, usually)	5.0×10^2 to $1.3 \times 10^{4\ddagger}$	Linear	12,17,30,31
Levan (Fructan)	[6]- β DFruf $(2 \rightarrow)_n$ (Main) β DFruf $(2 \rightarrow 1)$ β DFruf (Branches)	1×10^4 to 1×10^8	Branched	31-34

Glc p = Glucopyranosyl, Fruf = Fructofuranosyl, Gal p = Galactopyranosyl²¹

[‡]Bacterially produced inulin has been reported to be branched and have a significantly higher molecular weight than plant derived inulin, see also table 3.2.³⁵

ISOLATION AND PRODUCTION

Inulin is predominately isolated from chicory root. The isolation process of inulin basically consists of 3 steps: (1) extraction of water soluble components, including inulins, from chicory root (2) purification to remove foreign compounds and optionally low DP inulins and (3) spray drying. Sometimes the extracted product is partially hydrolyzed to reduce the DP of the final product.³⁹ Here isolation and purification are only discussed briefly, for further reading on this topic the reader is directed to the review of Apolinário *et al.*⁴⁰

Inulin extracted from chicory root contains up to 10% of sugars (mono- di- and small oligosaccharides).⁵ Typically, extraction is done by boiling the cleaned and cut or ground up roots in water. Process conditions such as pH of the water, water-root ratio, boiling time *et cetera* may vary.^{41,42} As will be described in section *Chemical stability*, pH and boiling time could affect the DP of the produced inulin. After extraction, the obtained mixture is condensed through evaporation.

Purification of inulin is mostly done by making use of the solubility difference of the DP fractions present in extracts. Heating and cooling in combination with filtration, decantation and (ultra)centrifugation have been described to produce different molecular weight fractions of inulin.⁴²⁻⁴⁷ Alternatively (organic) co-solvents, such as methanol, ethanol and acetone, can be used to selectively precipitate long chain (DPn 25-40) inulin.⁴⁸ Inulin that

has not been precipitated in these processes can be turned into a solid by (spray) drying. Optimization of the spray drying process, by varying inlet air, solution temperature and feed pump speed, based on microstructure of the produced inulin and rheological behavior of concentrated inulin solutions have been described by Toneli *et al.*^{47,49}

Ronkart *et al.*⁵⁰⁻⁵³ investigated several aspects of the isolation and purification of inulin, with emphasis on the physical characteristics of the produced inulin. They investigated the influence of several parameters, such as feed and inlet temperature during spray-drying on the physicochemical characteristics of the produced inulin. It was found that at a feed temperature of 80 °C and higher, the produced inulin was completely amorphous. A high air inlet temperature (230 °C compared to 120-170 °C) also increased the amount of amorphous inulin produced. Next to that, they characterized oligofructose produced by hydrolysis of inulin from globe artichoke by endo-inulinase.¹⁷

Apart from extraction from plants, inulin can also be produced enzymatically. Inulosucrase type fructosyltransferase can synthesize inulin from sucrose by catalyzing both transglycosylation and hydrolysis of sucrose.⁵⁴ Several procedures to do so have been described, these mostly involve enzymes derived from bacteria. Enzymes from *Bacillus species 217C-11* have been used to produce inulin on a large scale⁵⁵ and *Escherichia coli* and *Streptococcus mutans* derived fructosyltransferase can produce very high molecular weight inulins.⁵⁶ Both these studies reported remarkably low polydispersity (around 1.1) of the produced inulin. Inulin producing fructosyltransferases from several *Lactobacillus* strains have also been characterized.^{57,54} Inulosucrase from *Leuconostoc citreum* CW 28 was shown to produce different molecular weight inulin when it was cell associated compared to when it was free in solution.⁵⁸ The cell associated enzyme predominately produced inulin with a molecular weight between $1.35-1.60 \times 10^6$ Da and the free enzyme produced more inulin with a molecular weight between 2600 and 3400 Da.⁵⁸

Isolation of two plant derived fructosyltransferases from *Helianthus tuberosus* and the production of inulin with those purified enzymes was described by Lüscher *et al.*⁵⁹ The fungus *Aspergillus oryzae* KB is also able to produce inulin type oligofructoses from sucrose, but additionally possesses another enzyme which simultaneously hydrolyzes sucrose. The first enzyme produces 1-kestose, nystose and fructosyl nystose, whereas the second one produces glucose and fructose.⁶⁰ Oligofructoses can be produced by partial enzymatic hydrolysis of polyfructoses. Enzymes from *Aspergillus niger* can produce oligofructose from both hydrolysis of inulin (by inulinase) and synthesis from sucrose (by β -fructosyltransferase) and its inulinases provided higher yields than inulinases from *Kluyveromyces marxianus*.⁶¹ Beghin-Meiji, a commercial supplier of oligofructose, use β -fructo-furanosidase from *Aspergillus Niger* to synthesize, rather than to hydrolyze, oligofructose from sucrose.⁶² For more information on microbial enzymatic production of oligofructoses, either from synthesis from sucrose or from hydrolysis of inulin, the reader is directed to a recent review of

Mutanda *et al.*⁶³ on this topic. To the best of our knowledge, high molecular weight inulin from synthetic source is not yet commercially available on a large scale, most likely because of the high production costs.

Finally, a completely different method of production is the genetic modification of a potato to make it produce inulin like globe artichoke. However the inulin yield is low (5%) and inulin production goes at the cost of starch production.⁶⁴ Van Arkel *et al.*⁶⁵ recently published a review on plants that were genetically modified to produce inulin. They named modified sugar beet, sugarcane and rice as potential candidates for production of inulin, with possibilities to control certain characteristics (e.g. chain length) of the produced inulin by selectively controlling the expression of specific synthesizing enzymes.

USES

Inulin is widely applied in the food industry and it serves many purposes. It has been used as a (low calorie) sweetener, to form gels, to increase viscosity, to improve organoleptic properties, and as a non-digestible fiber. Mostly it is used as a sugar and fat replacer in dairy products and as a prebiotic. Examples of use in dairy are application in cheese, milk, yogurt and ice cream.⁶⁶ Some examples of use of inulin in non-dairy food are use in bread, biscuits, cereal and meat products.⁶⁷⁻⁷⁰ Previous reports have already extensively reviewed the food applications of inulin,^{9,12-14,30,39,66,71} as well as its prebiotic effects.^{12,13,15,72,73}

Applications of inulin as pharmaceutical excipient are even more diverse and range from stabilization of protein-based pharmaceuticals,⁷⁴ through solid dispersions to increases dissolution rate,⁷⁵ to targeted colon delivery.¹⁶ Moreover, as mentioned earlier, inulin itself is used as a diagnostic tool for measuring the kidney function (glomerular filtration rate).^{10,11} Inulin is injected intravenously, after which it is excreted renally. As inulin is neither naturally present in nor metabolized in the circulation, the amount of inulin secreted in the urine provides information on kidney function. Less widespread is the use of inulin for industrial and chemical purposes. Stevens *et al.*⁷⁶ reviewed the derivatization of inulin and applications of these chemically modified inulins for a wide range of applications, from inhibiting calcium carbonate crystallization industrially to use in hair gel.

The section *Physicochemical characteristics* will address the physicochemical characteristics of inulin. These characteristics are what make inulin such a versatile substance. For example, inulin is used in food as a texture modifier and fat replacer because of its DP-dependent gel forming and viscous behavior (see section *Rheology*). The (2→1) glycosidic bonds of inulin make it indigestible to humans and it can therefore be used as a low-calorie sweetener, fat replacer and dietary fiber.³⁰ Colonic microorganisms such as lactobacilli, however, are capable of breaking down this bond, making inulin suitable for colonic targeting. The relatively high glass transition temperature of amorphous inulin (section *Thermal characteristics and physical stability*) in combination with its flexible backbone makes it a good stabilizer of proteins applied both pharmaceutically⁷⁷ and in food.⁷⁸ Lastly, specific crystalline morphologies (section *Morphology*) make inulin suitable as an adjuvant for vaccines.⁷⁹

PHYSICOCHEMICAL CHARACTERISTICS

CHAIN LENGTH

As mentioned in the introduction the DP of inulin determines to a substantial extent its physicochemical characteristics. Table 3.2 provides an overview of the reported DPs of different types of inulin to serve as a frame of reference. It is, however, to be noted that the degree of polymerization alone oversimplifies reality, as it does not take into account the distribution of the different fractions. Also, in many cases no distinction is made between the DPw and DPn (thus nor between the weight and number based molecular weights (Mw and Mn)), which are only identical when the material is monodisperse. Where a degree of polymerization without further specification was reported, it was assumed to be the number based variety. For inulin the DPn can be converted into the average molar mass using equation 3.1. Similar can be done for DPw by substituting DPn by DPw and Mn by Mw. Table 3.2 contains reported DP and molecular weight values of inulin from various sources as reported in literature, it was not completed with calculated values for clarity purposes.

$$(3.1) \quad M_n = 180 + 162 \times (DP_n - 1)$$

Wada *et al.*⁵⁵ reported that the main difference between the inulin they synthesized enzymatically and plant-derived inulin was the polydispersity. Synthetic inulin had a lower polydispersity, which they illustrated with chromatograms from HPAEC with pulsed amperometric detection. Unfortunately, however, the polydispersity was not quantified.

MORPHOLOGY

Crystal morphology

Lis and Preston⁸⁴ patented the production of obloid and needle-like shaped crystals of inulin. The needle-like crystals were 1-20 μm in length with the other axes being 10-30% of that. The obloid crystals were of the same length, yet the other axes were sized at 50-80% of the length. The different types of crystals were produced by cooling an aqueous liquid containing 10-50% of Fibruline Instant (DP 6-12). The crystal transition temperature of the two crystals was approximately 75-95 °C. If the solution was cooled from a temperature higher than the crystal transition temperature obloid crystals would be produced, if lower (given all inulin was previously dissolved) needle-like crystals were obtained.⁸⁴ It was argued that the mouth feel of the obloid shaped crystals is better than that of the needle shaped crystals. Viscosity could be altered by varying the ratio and sizes of the two types of crystals. Needle-like crystals predominately increased viscosity while obloid ones improved lubricity.

Table 3.2 Overview of size and origin of different inulins.

Manufacturer	Product name	Source	DP	Molecular weight	DPw/DPn	Article cited
Orafti	Raftilose P95	Chicory	DPn 4-5	Mn 624-679		80,81
	Raftiline ST	Chicory	DPn 10-12	Mn 1250		80,82
	Raftiline HP	Chicory	DPn 21-26, DPw 31	Mn 2499		19,55,82,83
	RS	Chicory	DPn 14.2; DPw 19.4		1.13	74
Cosucra	Fibrulose F97	Chicory	DPn 5.5			81
	Fibruline Instant	Chicory	DPn 9			81,84
	Fibruline LCHT	Chicory	DPn 20-22, DPw 26.4		1.3	37,81
	Fibruline XL	Chicory	DPn 20-23, DPw 27-30			19,50,85
Imperial Sensus	SC 95	Chicory	DPn 5.5, DPw 6.0		1.09	74
	Frutafit CLR	Chicory	DPn 7-9			86
	Frutafit	Chicory	DPn 9	Mn 832		82
	Frutafit IQ	Chicory	DPn 8-12			86,87
	Frutafit Texl, EXL	Chicory	DPn \geq 23, DPw 26.2		1.3	74,86
Sigma	Inulin	Chicory	DPn 25	Mn 4450, Mw 4620-6200		55,80,88-90
	Inulin	Jerusalem Artichoke	DPn 29	Mw 3400 \pm 150		55,89
	Inulin	Dahlia	DPn 26- 35			55,88,91
N.C.P.*	n/a	Jerusalem Artichoke		Mw 7200 \pm 100 Mn 6100 \pm 500	1.18	92
N.C.P.*	n/a	Jerusalem Artichoke	DPn 28-33	Mn 4900-5600 \pm 500		41
Beghin-Meiji	Actilight 950P	<i>Aspergillus niger</i>	DPn 3	Mn 579		80,81
N.C.P.*	n/a	<i>Bacillus sp. 217C-1</i>	DPn 16-18			55
N.C.P.*	n/a	Globe artichoke	DPn 80			17
N.C.P.*	n/a	<i>Aspergillus sydowi</i>		Mw 1.49 \times 10 ⁴ -5.29 \times 10 ⁶	1.13-3.01	93
N.C.P.*	n/a	<i>Aspergillus sydowi</i>		Mw 26-28 \times 10 ⁶	1.7	35
N.C.P.*	n/a	synthetic FTF <i>Streptococcus mutans</i>		Mw 30-90 \times 10 ⁶	1.1	35,56

* N.C.P. = non-commercial product, purified or produced by the authors, n/a = does not apply

Hébette *et al.*⁸³ investigated the influence of cooling rate, molecular weight, concentration, and storage time on the crystallization of inulin using Raftiline ST (DP 10-12) and fractions thereof. The crystallization produced obloid, or more accurately eight-shaped, crystals which were 5-20 μm in size if they started forming at a high temperature (77 °C) and up to a tenfold smaller if they were formed at lower temperatures (65 °C). The thickness and perfection of the formed crystalline lamellae was inversely related to the amount of undercooling. By small angle X-ray scattering (SAXS), they found that the crystal structure was the same as the monohydrate form reported by André *et al.*⁹⁴ (see below). The periodicity of the crystals produced at higher temperatures was 110 Å and at lower temperatures 90 Å.

Crystal structure

Marchessault *et al.*⁹⁵ investigated the three-dimensional crystal structure of inulin. They reported it to have a 5-fold helix, being either left- or right-handed with a space of 2.16 Å per monomer and thus 10.8 Å per loop. Reported bond angles were $\Psi 130^\circ$, $\phi 75^\circ$ and $\omega = 60^\circ$ (right-handed) or $\omega = 180^\circ$ (left-handed), see figure 3.2 for an illustration of which bond-angles are described. Large differences in crystal structure were shown between polyethylene glycol and inulin, which were explained by steric interactions between the substituents and the exo-anomeric effect.⁹⁵

André *et al.*⁹⁴ claimed Marchessault's findings of an unusual 5-fold helix to be based on limited data and in fact incorrect and that the crystals they produced actually contained a 6-fold helix. They reported the formation of an orthorhombic hemi-hydrate crystal with dimensions of $a=16.70$ Å, $b= 9.65$ Å, $c=14.4$ Å per 6 units and a pseudo-hexagonal monohydrate crystal with $a=16.70$ Å, $b=9.80$ Å, $c=14.7$ Å per loop. The hemi-hydrate contained one water molecule per two fructosyl residues while the mono-hydrate had one per fructosyl residue. The helical conformation of the hemi-hydrate was characterized by $\phi = 66^\circ$, $\psi = 154^\circ$, and $\omega = -82^\circ$ and the monohydrate's dimensions were very similar with the following bond angles $\phi = 68^\circ$, $\psi = 159^\circ$, and $\omega = -87^\circ$. André thus concluded that the progress per loop was 14.4 or 14.7 Å as opposed to 10.8 Å.^{94,96} It should however be noted that the methods used to produce the crystals by André and Marchessault were not identical and the inulin used was not characterized apart from crystal structure. As described in section *Crystal morphology*, the method of production is of influence on the morphology of the produced crystals and thus it is possible that different isoforms might have been produced. Further down several isoforms of inulin monohydrate will be discussed based on classifications of solubility and size.

Structure in solution

French³² calculated the theoretically allowed conformations for inulin in solution and concluded that the allowed conformations were similar to those of dextran. Of course the reported conformations are merely the allowed conformations based on specific assumptions, French also noted that there are a lot of factors influencing the favored structure of oligosaccharides. Vereyken *et al.*⁹¹ also found many possible conformations for inulin in their models, including a zigzag conformation with the ω angle at 180° which stayed stable in their simulations. This multitude of possible conformations shows the molecular flexibility of inulin. Several reports have described the behavior of a broad range of inulins in solution. Models and measurements by Oka *et al.*⁹⁷ and Liu *et al.*⁹⁸ indicate that a helical conformation is possible for oligofructose of DP 5. This conformation would however not be possible for higher molecular weight inulins due to steric hindrance. Liu *et al.*⁹⁸ reported that for inulins sized up to DP 9 simple helical structures are not the predominant structure and Oka *et al.*⁹⁷ found that for a DP of 8 and higher the backbone would reach a more rigid conformation. It thus seems that an organized three-dimensional structure does not occur for oligosaccharides with a DP smaller than about 8 or 9.

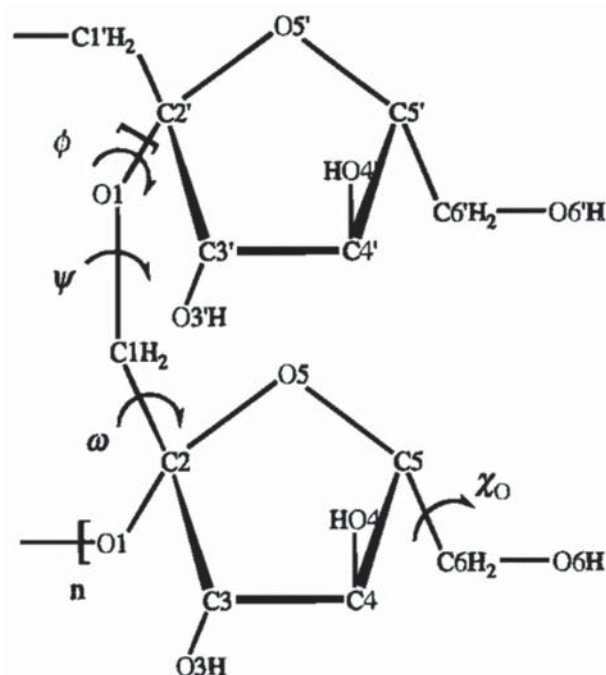


Figure 3.2 Representation of the atomic labeling scheme for the inulin chain. Reprinted with permission from André *et al.*⁹⁸. Copyright 1996 American Chemical Society.

SOLUBILITY

Wada *et al.*⁵⁵ investigated the aqueous solubility at various temperatures of three different types of inulin, two Raftiline inulins which differed in size and an enzymatically produced synthetic inulin. Their results are depicted in figure 3.3, raftiline HP (DPn 23-25) displays lowest solubility, followed by Raftiline ST (DPn 10-12). What is remarkable, however, is that the enzymatically produced synthetic inulin (DPn 16-18) had a higher solubility than raftiline ST despite its higher DP. Normally the solubility of polymers decreases with increasing DP. As mentioned, the average DP of a polymer only tells part of the story and it is also relevant to consider the molecular weight distribution of the different DP fractions. The reader is directed to the cited article for molecular weight profile chromatograms of these inulins. The absence of highly polymerized fractions (no fraction with a DP larger than 30) in the enzymatically produced synthetic inulin could explain the higher solubility of the synthetic inulin.⁵⁵ Unfortunately, the method by which solubility was established was not described. Kim *et al.*³⁸ also investigated the solubility of Raftiline HP over a temperature range and also found a low solubility up to 50 °C from where on the solubility drastically increased until 35% at 90 °C. Reported aqueous solubilities of some other inulines are listed in table 3.3. Bot *et al.*¹⁰¹ reported hazing when dissolving Raftiline ST inulin in water. This was presumably the result of a small, high-DP crystalline fraction of inulin which did not dissolve readily. It was found that this fraction did not dissolve at room temperature, but typically would do so at temperatures of 60°C and higher.

Cooper *et al.*^{102,103} initially identified four polymorphs of crystalline inulin (α , β , γ and δ) based on their dissolution behavior. β inulin, which was produced by addition of ethanol or by freeze-thawing, is readily soluble in water at room temperature. The other polymorphs, which could be interconverted into more stable versions (in the order β , α , γ to δ), required

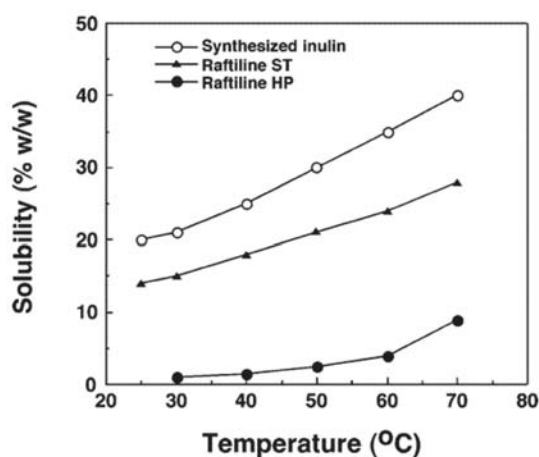


Figure 3.3
Differences of aqueous solubility between plant-origin (DPn10-12 and 23-25) and enzymatically synthesized inulin (DP 16-18). Reprinted with permission from Wada *et al.*⁵⁵. Copyright 2005 American Chemical Society.

Table 3.3 Aqueous solubilities of different sizes of inulin at various temperatures

DPn or Mw (g/mol)	Solubility	Temperature (°C)	Article cited
4	>75% (w/v)	25	39
12	12% (w/v)	25	39
25	2.5% (w/v)	25	39
4468 g/mol	~10% (w/w)	30	99
8-12	17.4% (w/w)	37	100

higher temperatures to dissolve. The γ polymorph was made up only out of inulin with a molecular weight > 8000 g/mol, where the α and β forms also contained lower molecular weight inulin fractions.¹⁰² More recently the list of polymorphs was expanded to seven plus the amorphous form.¹⁰⁴ All the polymorphs, which differed in chain length, were monohydrate inulin crystals described earlier.^{94,105} The monohydrate and hemi-hydrate only differ in the amount of water associated to the inulin, not in their crystal structure.^{96,106} As suggested by André *et al.*⁹⁴, the fructose units of inulin formed helices with a 6-unit repeat. Cooper *et al.*¹⁰⁵ found that the different polymorphs increased in size by steps of 6 fructose units and concluded that these units formed additional helical turns. Surprisingly, these polymorphs were characterized by a degree of polymerization of $6n+1$, rather than $6n$. This additional fructosyl residue was shown to be able to link to glucose of another molecule through hydrogen bonding, allowing formation of tertiary structures of inulin.¹⁰⁷

Ronkart *et al.*⁵⁰ found that increasing the feed temperature during spray drying reduced crystallinity and increased the T_g of the produced samples. As a higher T_g is correlated with a higher molecular weight (see section *Glass transition temperature (T_g)*), this too indicates that the crystals that dissolve at higher temperatures are made up out of higher molecular weight inulins.

In summary, inulin is poorly soluble in water, with decreasing solubility for higher molecular weight fractions. Solubility increases at higher temperatures for all different inulins. These characteristics enable a controlled production of several isomorphs, allowing modification of product characteristics such as rheology. Glibowski¹⁰⁸ however reported difficulties in controlling inulin crystallization.

Inulin is hardly soluble in ethanol,⁸⁷ explaining the use of ethanol in precipitating inulin,¹⁰² it is freely soluble in dimethyl sulfoxide (DMSO) and very poorly to sparingly soluble in isopropanol.^{99,90,89,109} Phelps *et al.*¹¹⁰ reported that crystals produced using ethanol-recrystallization contained more low DP inulin compared to water-recrystallized samples. Considering that ethanol reduces the solubility of inulin so drastically, one would indeed expect that lower DP fractions of inulin are also affected and separate from solution.

RHEOLOGY

Viscosity

Multiple reports have appeared on the intrinsic viscosity of several inulins in different media, the results of which have been summarized in table 3.4. The intrinsic viscosity decreases by addition of salts and increases with increasing DMSO concentration and molecular weight. The dynamic viscosity of several types of inulin at specific concentrations and temperatures has also been reported, an overview can be found in table 3.5.

Like table 3.4, table 3.5 also shows an increase in viscosity with increasing molecular weight. With increasing temperature, the viscosity is reduced. Wada *et al.*⁵⁵ reported a slightly lower viscosity for enzymatically produced synthetic inulin (DPn 16-18) than for two commercial Raftiline samples (ST with a DPn of 10-12 and HP with a DPn of 23-25) despite the fact that it has a higher molecular weight than Raftiline ST. However, as explained in section *Solubility* the average molecular weight does not provide information about the size distribution. The enzymatically produced synthetic inulin lacks highly polymerized fractions, which could be an explanation for this difference in viscosity. Wada *et al.*⁵⁵ only presented the viscosity data graphically and they were thus not added to table 3.5.

Hydrodynamic shape

The Mark-Houwink equation (equation 3.2) defines the relationship between intrinsic viscosity ($[\eta]$) and molecular weight (M) for polymers, with two constants (K and a).^{109,35}

$$(3.2) \quad [\eta] = K \times M^a$$

The constant a in this equation is indicative for the shape of the polymer in the solution. The a-value for compact spheres is 0, whereas an a-value below 0.5 indicates branched structures, an a value between 0.5-0.9 is associated with a random coil, and an a-value over 2.0 with a rod structure.³⁵ Intermediate a values represent intermediate shapes.

The plots in figure 3.4 from the publication of Wolff *et al.*³⁵ show linear correlations between Mw and intrinsic viscosities for inulin species with a Mw > 5.0 × 10⁴ and for species with a Mw < 5.0 × 10⁴. They found that a = 0.71 for the 'small' inulins, showing a random coil structure and a=0.02 for the high molecular weights, indicative of a compact sphere. Remarkably these results are similar to those reported for levan, which does not have a polyethylene glycol-like flexible backbone. Apparently these bacterially produced fructans have similar characteristics, despite differences in their backbone structure, branching may explain the found similarities.³⁵ In addition, it should be noted that levan is still quite flexible compared to other polysaccharides like amylose, as it is linked via the C6 carbon (a primary alcohol) and not directly to the ring.

Table 3.4 Intrinsic viscosity ($[\eta]$) of inulin in several media at various temperatures (T)

Medium	$[\eta]$ (mL/g)	Kh (-)	T(°C)	Mw (g/mol)	Source (manufacturer)	Article cited
Water	4.92	1.13	30	4450	Chicory root (Sigma)	90
Water	4.49	1.10	30	4478	Chicory root (Sigma)	109
Water	5.85	n.r.	25	1.49×10^4	<i>A. sydowi</i>	93
Water	6.97	n.r.	25	1.87×10^4	<i>A. sydowi</i>	93
Water	8.26	n.r.	25	2.38×10^4	<i>A. sydowi</i>	93
Water	10.5	n.r.	25	3.37×10^4	<i>A. sydowi</i>	93
Water	12.8	n.r.	25	7.52×10^4	<i>A. sydowi</i>	93
Water	16.3	n.r.	25	16.6×10^4	<i>A. sydowi</i>	93
Water	16.5	n.r.	25	60.4×10^4	<i>A. sydowi</i>	93
Water	16.5	n.r.	25	97.4×10^4	<i>A. sydowi</i>	93
Water	18.6	n.r.	25	178×10^4	<i>A. sydowi</i>	93
Water	19.1	n.r.	25	529×10^4	<i>A. sydowi</i>	93
Water	18	n.r.	25	54×10^6	FTF from <i>S. Mutans</i>	35
Water:DMSO(3:1)	5.86	2.12	30	4450	Chicory root (Sigma)	90
Water:DMSO(2:1)	6.63	1.50	30	4450	Chicory root (Sigma)	90
Water:DMSO(1:1)	7.96	1.27	30	4450	Chicory root (Sigma)	90
Water:DMSO(1:2)	11.0	1.09	30	4450	Chicory root (Sigma)	90
Water:DMSO(1:6)	14.9	1.75	30	4450	Chicory root (Sigma)	90
DMSO	18.8	1.30	30	4450	Chicory root (Sigma)	90
DMSO	15.2	0.48	30	4478	Chicory root (Sigma)	109
DMSO	9.1±0.2	n.r.	25	3400 ±150	Jerusalem artichoke (Sigma)	89
DMSO	10.7±0.2	n.r.	25	6200 ±200	Chicory root (Sigma)	89
0.5M NH ₄ SCN (in water)	3.65	2.40	30	4478	Chicory root (Sigma)	109
0.5M NaCl (in water)	4.30	2.16	30	4478	Chicory root (Sigma)	109
0.5M Na ₂ SO ₄ (in water)	4.21	2.24	30	4478	Chicory root (Sigma)	109

Kh = Huggins constant (if the Huggins formula was used to calculate the intrinsic viscosity), n.r. = not reported.

Table 3.5 Reported dynamic viscosities of several sizes of inulin in water.

Viscosity (mPa.s)	T (°C)	Concentration (%)	DPn	Article cited
<1.0	10	5	4	39
1.6	10	5	12	39
2.4	10	5	25	39
1.21±0.06	25	5	28	41
1.27±0.08	25	5	30*	41
1.29±0.09	25	5	30*	41
1.31±0.11	25	5	33	41
1.12	37	10	8-12	100

*Samples are from two different subspecies of Jerusalem artichoke.

Next to viscosity, static light scattering was also used to determine the influence of molecular weight on the radius of gyration of the bacterially produced inulins. Those results too indicated a compact globular shape for high MW inulin, but more importantly showed that there might be a difference in branching architecture for inulins of different origins.³⁵ Using small angle x-ray scattering, Eigner *et al.*⁹² showed that inulin from *Jerusalem Artichoke* with a Mw of 7200 had a rod-like formation in aqueous solution. This is not consistent with the above mentioned conclusions for bacterially produced inulins. The most likely explanations for this are the enormous difference in molecular weight between bacterially produced and natural inulin (see table 3.2) combined with the amount of branching of the bacterially produced inulins and the lack thereof in natural inulins.

Azis *et al.*⁸⁹ investigated characteristics of inulin extracted from Jerusalem artichoke and Chicory root (Mw 3400 ±150 and 6200 ±200, respectively) in DMSO. They differed significantly in size, but a lot less in intrinsic viscosity, indicating a conformation between a random coil and a compact sphere in that solvent. Naskar *et al.*⁹⁰ concluded that inulin forms globular aggregates in aqueous solutions and rod-like or spindle-like assemblies in DMSO. In summary hydrodynamic shape and behavior of inulin are influenced by molecular weight, solvent and branching (depending on the inulin source).

De Gennaro *et al.*⁸⁰ investigated the hydrodynamic behavior of several inulins (ranging from oligofructose with Mn 579 to inulin with Mn 4620) by looking at apparent specific volume (ASV), isentropic apparent specific compressibility [$K_{2(s)}$] and spin-lattice relaxation times (T_1). ASV, a measure of hydrostatic packing with water molecules, was found to increase with degree of polymerization, indicating that low DP inulin had better hydrostatic packing and interacted with water more. Isentropic compressibility values can be interpreted as a measure for the compatibility between water and inulin. $K_{2(s)}$ increased with DP and concentration, showing reduced solute-water affinity. Inulin was found to be more water

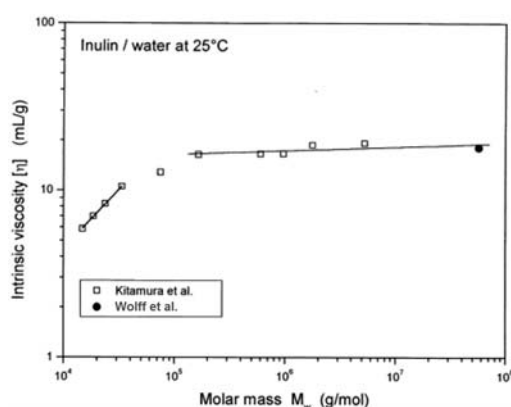


Figure 3.4

Molar mass dependence of intrinsic viscosity for high Mw bacterially produced inulin, data from Kitamura *et al.*⁹³ and Wolff *et al.*³⁵ Lines represent the linear regression of the Mark-Houwink equation (equation 3.2).^{93,35}

compatible than other tested carbohydrates except at high concentrations (>15% (w/w)) and/or for a DP of 9 or higher. In the light of the discussion above the latter could mean that the formation of three-dimensional helical structures reduces inulin's water compatibility. Lastly, due to an increased order of protons and reduced water mobility, T_1 values decreased with increasing Mn and concentration.⁸⁰

Gelling

In general inulin gels are based on the interactions occurring between dissolved inulin chains. However, inulin gels may also still contain undissolved microcrystals. These microcrystals can be interconnected, forming a network that is able to interact with both the solvent and other inulin particles thereby increasing gel strength.^{38,39,101,85,111} As described earlier, temperature and molecular weight influences the formation of microcrystals and thereby also gel formation. Based on this and their higher viscosity, high molecular weight inulins are better gel formers than their lower molecular weight counterparts. This also explains why hydrolysis, which reduces the degree of polymerization, reduces gel formation by disturbance of the network.¹¹² Using nuclear magnetic resonance spectroscopy, Van Duynhoven *et al.*¹¹¹ showed that lower inulin concentrations lead to lower concentrations of crystalline material. This results in a reduction in the network formation, explaining lower mechanical strength of the gel.

Inulin gels can be formed either thermally, through heating and cooling, or by applying shear forces.³⁸ Kim *et al.*^{38,112} have investigated both methods of gel production extensively. Thermally produced gels were found to be stronger and smoother than shear induced ones. Gel production was dependent on temperature, heating time, concentration, pH and addition of other solvents. Addition of other solvents (ethanol or glycerol) reduced polarity of the solution causing less solvent-inulin interactions, resulting in faster gel formation but with similar gel strengths. The minimal concentration of inulin needed for gel formation differed with temperature. The solution needed to be heated up to at least 40 °C to achieve gelling. However, heating to temperatures of 80 °C and higher, and acidic conditions (pH < 3) lead to substantial hydrolysis of inulin, resulting in reduced gel formation.³⁸ In these studies, only Raftiline HP (DPn 23-25) was used, the influence of molecular weight was thus not taken into account. Meyer *et al.*⁶⁶ did investigate the influence of DP and concentration on gel strength. They found that higher molecular weight inulins produce stronger gels and are able to form gels at lower concentrations as can be seen in figure 3.5.⁶⁶

Chiavaro *et al.*¹¹³ specifically investigated the influence of DP on thermal gelation and found that by using inulin of different molecular weight gels could be produced with different characteristics due to a difference in balance between solid-solid and solid-liquid interactions. Using texture profile analysis, higher molecular weight inulins were found to form gels that were harder, more adhesive and less cohesive both after production and after storage at

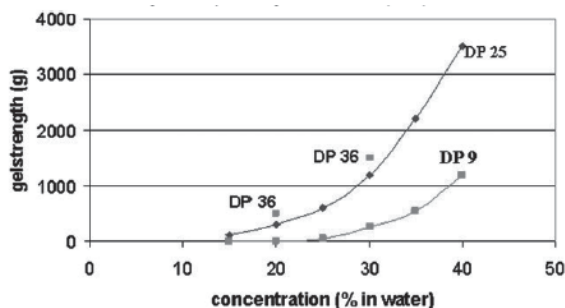


Figure 3.5

Gel strength in relation to concentration of different inulin types. The gels were prepared by heating the solutions at given concentrations to 85°C and allowing them to cool overnight at 4°C.⁶⁶

4 °C for 4 weeks. This means that higher molecular weight gels required more force to be deformed, would stick to surfaces more and had weaker internal bonds between components.¹¹⁴ The gels prepared from higher molecular weight inulin had more freezable water in comparison to gels prepared from low molecular weight inulin.¹¹³ These observations were ascribed to an increase in inulin-inulin interactions and a decrease in inulin-water interaction with increasing molecular weight. As solid-solvent interactions were needed for storage stability, lower molecular weight inulin gels maintained their textural characteristics better during storage. Here too, the average DP does not tell the complete story and the polydispersity should be taken into account as well. It seems that for a stable gel a fraction of the inulin needs to be of high enough DP for micro-crystallization and solid-solid interactions to form a network, and another part needs to be smaller to interact with the solvent.¹¹³ This is in line with the findings Glibowski *et al.*¹¹⁵ that addition of low concentrations ($\geq 0.02\%$) of seeding crystals allowed heated inulin solutions to form gels instead of precipitating during cooling. At a higher concentration of seeding crystals ($\geq 0.4\%$) stronger and more stable gels were obtained.

Shear-induced gels were reported to become smoother when the applied shear stress was increased.³⁸ This is because low shear caused the formation of larger aggregates; at higher shear stresses a better dispersion was achieved. In comparison to thermally produced gels, shear gels contain larger particles with a broader particle size distribution and with that the gels have a reduced yield stress. Ronkart *et al.*⁸⁵ found that repeated application of high shear stress reduced particle size, facilitating the formation of a finer network of particles and textural modifications. In addition, the reduction in particle size might have resulted in more inulin dissolving, increasing viscosity and also modifying gel behavior. Bot *et al.*¹⁰¹ investigated how several methods of crystallization influenced the large deformation rheology of inulin gels and found that shape and size of the produced crystals play an important role in the formed network and thus the texture of the produced gel.

Using high-pressure homogenization, Alvarez-Sabatel *et al.*¹¹⁶ related gel characteristics to pressures used during this process. It is important to note here that the product temperature increases during processing and that this temperature increase is much larger for higher processing pressures. Caution should therefore be taken in relating processing pressures to gel characteristics directly, as this heating also influences the characteristics of the formed gel.¹⁰⁸ Nonetheless, by varying this pressure and therewith the product temperature, inulin gels with specific characteristics can be produced.

Gelling and texture modifying properties of inulin in more complex systems have been reported. Some reports suggest that inulin has a synergistic effect on gelation with other gelling agents (e.g. gelatin, alginate, maltodextrins and starch) and proteins whilst others actually report inulin competing with them.^{39,66,71,117,86,118} It seems that for some excipients a competition for water occurs whilst with others a combined network is formed, but it goes beyond the scope of this review to discuss this behavior in detail here.

Lastly, several reports described the synthesis and behavior of (meth)acrylated inulin gels for controlled release of drugs in the colon.¹¹⁹⁻¹²⁷ Gels of these chemically modified inulins were produced by formation of covalent cross-links between the added side-chains using free radical polymerization. In terms of rheological behavior, a higher degree of substitution resulted in a faster gelation process and higher rigidity of the obtained gels for methylacrylated inulin due to more inter-molecular crosslinking.¹²⁴ Different cross-linkers were investigated and found to modify rate of crosslinking and elasticity of produced gels differently, allowing for control of mechanical properties of these gels.¹¹⁹ Controlling the amount of swelling of the hydrogels is critical. High swelling of the gel is needed to allow degradation in the colon by bacteria,¹²² however, to prevent premature drug release before the colonic environment is reached, low swelling is key.¹²⁵ Recently, chemically crosslinking of inulin molecules using divinyl sulfone was used to produce microgels intended for controlled release in the stomach.¹²⁸

THERMAL CHARACTERISTICS AND PHYSICAL STABILITY

Glass transition temperature (T_g)

Most commercially available types of inulin are amorphous and can thus be characterized by a glass transition temperature (T_g). Above the glass transition temperature molecular mobility is strongly increased and crystallization can occur. Molecular weight influences the T_g of anhydrous carbohydrates and the T_g of the maximally freeze concentrated fraction (T_g') of carbohydrates.

The T_g' is of interest when freeze-drying is used as a production process. The T_g' should not be surpassed during the first part of freeze-drying (primary drying) in order to achieve an amorphous product. The Fox-Flory equation (equation 3.3) describes the relationship between T_g and molecular weight.¹²⁹

$$(3.3) \quad T_g = T_{g,\infty} - \frac{C}{M}$$

With $T_{g,\infty}$ being the Tg at infinite molecular weight, M molecular weight, and C a constant. The $T_{g,\infty}$ and constant C were calculated for inulin using data of Hinrichs *et al.*⁷⁴ and unpublished data. The maximal Tg ($T_{g,\infty}$) was 175 °C, with a fitting constant of 75 kDa. The maximal Tg' ($T_{g,\infty}$) was -14 °C with a fitting constant of 11.3 kDa. Compared to smaller carbohydrates like sucrose and fructose, inulin has a much higher Tg. At similar weights glucans have even higher Tg values. For the Tg' values the same trends apply.¹³⁰

Water acts as a plasticizer on amorphous carbohydrate samples, meaning it decreases the Tg. The Gordon-Taylor equation (equation 3.4) describes Tg of an ideal mixture of two amorphous components, in this case a mixture of water and inulin. Water has a very low Tg of approximately 165K, explaining why even small amounts strongly decrease the Tg.^{131,132}

$$(3.4) \quad T_{g, \text{mix}} = \frac{f_a * T_{g,a} + K * f_b * T_{g,b}}{f_a + K * f_b}$$

f_x is the weight fraction of component x (with x being either a or b), and K is usually considered as a fitting parameter.¹³³

Several papers have reported measurements of the influence of the water content on the Tg of inulin. Figure 3.6 shows the results of water uptake of up to 12% on the Tg of inulins of various molecular weights. The Gordon-Taylor equation was used to fit the curves. For all inulins, a water content of just 2% decreased the Tg with around 30 K and at a moisture content of 10% the Tg of the mixture had gone down by nearly 100 K.

Vapor sorption

Knowing that water can strongly reduce the Tg of a mixture, it is important to determine the water sorption of inulin in relation to relative humidity in the atmosphere. Using dynamic vapor sorption, water uptake of several inulins and trehalose was studied as a function of relative humidity (RH).⁷⁴ Water sorption was similar for all sizes of inulin and was similar to that of other amorphous carbohydrates. Trehalose crystallized at a RH above 50%, whereas the inulin samples remained amorphous on the timescale of the dynamic vapor sorption experiments (hours), even though they all surpassed their Tg during the measurement. This shows that inulin crystallizes less easily than trehalose. Incidental (short term) exposure to high relative humidity of amorphous inulin does therefore not necessarily lead to immediate crystallization. In two other studies where inulin was stored at controlled relative humidities for weeks, crystallization was found.^{82,134}

Ronkart *et al.*⁵¹⁻⁵³ described the consequences of moisture sorption for inulin samples with different degrees of crystallinity. Depending on the molecular weight of the inulin, the

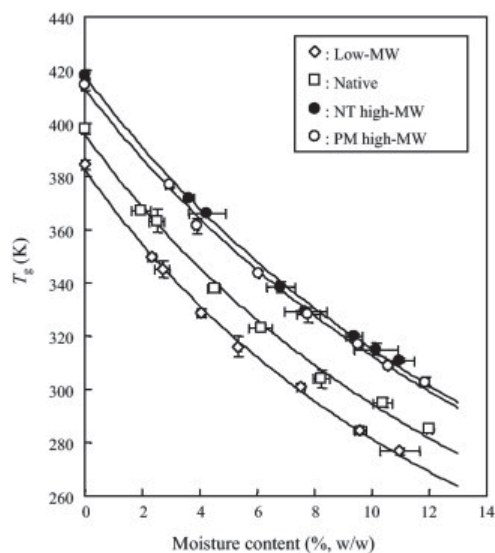


Figure 3.6
Effect of moisture content on T_g of several inulin samples. The low molecular weight (low-MW), native and high molecular weight (high-MW) samples had degrees of polymerization of respectively 7, 13 and 27. PM denotes pre-melted, meaning the sample had been heated in solution, quench-cooled and subsequently freeze-dried to make the sample completely amorphous, NT denotes not treated.¹³⁰

amorphous particles fused at RH of >56%⁵¹ or at RH over >75% at 20 °C⁵³ (corresponding to a water uptake of 12-15 g/100g dry inulin at >75% RH). This lead to caking, i.e. sticking together of the powder particles resulting in reduced flowability. The presence of crystals in the amorphous matrix limited the caking.⁵³ This behavior is not uncommon for polysaccharides.

They then defined three regions based on water uptake and crystallinity at 20 °C, as shown in figure 3.7.⁵² In region I inulin remained completely amorphous, in region III inulin was completely crystallized (and caked). Region II represents an intermediate region where inulin's macroscopic and thermal properties were changing. In region I the T_g of the samples was at least 10 °C above storage temperature, in region III the T_g was room temperature or lower. This shows that if the T_g drops below storage temperature +10 °C, mobility will increase and lead to crystallization and caking, which is nearly always undesirable. Therefore, storage conditions should be carefully chosen and exposure to high relative humidities and temperatures should be avoided.

Similarly, Schaller-Povolny *et al.*⁸² defined a critical moisture content (and corresponding critical relative humidity) based on macroscopical changes to inulin morphology, above which inulin would be crystalline. These large macroscopical changes are only truly apparent when crystallization is widespread and are therefore not a good measure for determination of a critical moisture content.⁵² The study does however show that inulins of different molecular weight pass through this critical point at different amounts of water uptake. Inulins with a higher molecular weight can withstand more water uptake before they reach

the critical point and thus be stored at higher RH. Higher molecular weight inulins may therefore be used to improve processability and storage stability in food or other products.⁸²

Melting temperature

Melting temperatures of fractions of Fibruline LCHT with different degrees of polymerization were determined and are shown in figure 3.8.³⁷ Two groups with different degree of crystallinity could be distinguished. The higher DP fractions were insoluble in water (obtained by precipitation in aqueous solutions at various temperatures), while the low DP fractions were produced by freeze-drying water soluble fractions.³⁷ Low DP fractions had a lower melting enthalpy, which is indicative for crystallinity, of 7-9 J/g and the higher fractions 17-19 J/g.³⁷ Even higher melting enthalpies ranging up to 47.6 J/g have also been reported.¹³⁴ Melting temperatures reported elsewhere were similar to the ones shown in figure 3.8, with melting temperatures being reported between 165 and 183 °C.^{41,56,109,134} The melting temperature of a enzymatically produced synthetic inulin as determined by Heyer *et al.*⁵⁶ was only 183 °C despite its much larger size (70×10^6 g/mol), which is common for polymers.¹³⁵ Inulin started degrading after melting, when heated above 200-225 °C.^{56,106,109} The hemi-hydrate of inulin (produced by water sorption of amorphous inulin) had a melting temperature of around 155-160 °C and the mono-hydrate (seeding crystals) had a melting point between 170-180 °C.¹⁰⁶ Similar melting temperatures were reported for the different monohydrate polymorphs described in section *Solubility*, which differed from each other in molecular weight.¹⁰⁴ It is therefore likely that the two different fractions shows in figure 3.8 are mono-hydrate and hemihydrate forms of inulin.

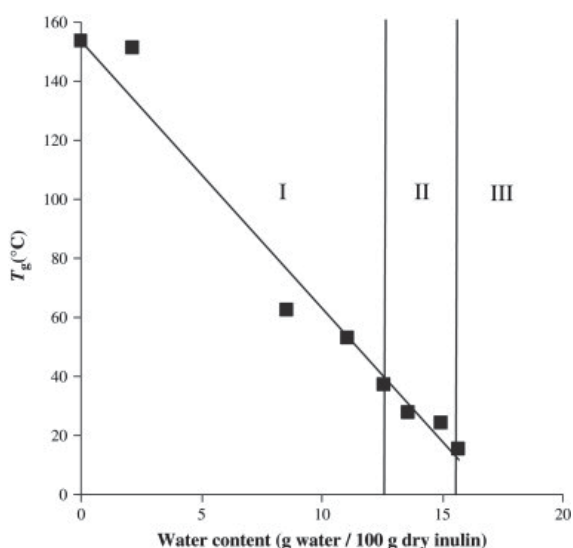


Figure 3.7
Glass transition temperature-water content relationship for inulin DPn 23/ DPw 30 with three regions of different crystallinity.⁵²

CHEMICAL STABILITY

Inulin with a glucose end group does not have or form any reactive aldehyde or ketone groups and is therefore non-reducing. However, inulin molecules lacking this glucose end group, thus ending with a fructose group, are reducing.¹³⁶ Furthermore, as discussed previously, inulin is a polydisperse mixture and can also contain mono- and disaccharides which are more reactive. These inulins without glucose end group can thus take part in reactions with other components, such as the amino group of proteins in the Maillard reaction. In the light of the above, it could be useful to distinguish between inulin with and without glucose end groups. If reducing groups are present and the Maillard could potentially occur, formulation modifications such as the addition of sulfite, or adjusting the pH could be used to reduce the risk of the Maillard reaction occurring.¹³⁷

Several reports discussed the amount of reducing groups of inulin, some supplied more details than others.^{74,76,80} Stevens *et al.*⁷⁶ found a residual reducing activity of 0.5-2.5% after removal of mono- and disaccharides from 'native inulin'. Hinrichs *et al.*⁷⁴ found that the percentage of carbohydrate units containing reducing groups was much higher for small inulins in comparison to larger inulins. Oligofructose synthesized from sucrose had fewer reducing groups than oligofructose produced by hydrolysis of inulin.⁸⁰ Hydrolyzed inulin will contain fructose chains both with and without glucose end group, whereas inulin synthesized from glucose only contains fructose chains with a glucose end group. The relative abundance of fructose chains without glucose can explain the difference in amount of reducing groups between these two production methods.

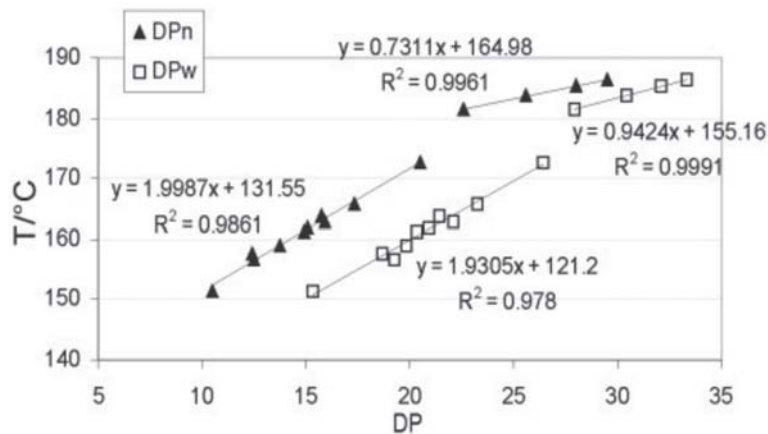


Figure 3.8 Relations between degree of polymerization (DP) and inulin's melting temperature.³⁷

Influence of several processing parameters on the amount of reducing groups of inulin were reported.^{38,112} Reducing sugar content of aqueous inulin solutions increased with increasing temperature and with lower pH due to hydrolysis of inulin.³⁸ At neutral pH, the percentage of reducing groups increased from <0.1% to only 1.2% after heating a concentrated solution to 100 °C for 5 minutes. At pH values of 3 or lower the amount of reducing sugars formed increased drastically, up to 25% at pH 1.³⁸ Reducing groups were formed as a result of hydrolysis, which followed pseudo first-order kinetics with reducing activity increasing continuously over time during heating.¹¹² Since hydrolysis was the cause of the increase in reducing activity, it was indirectly indicative of a reduction of DP. This is because hydrolysis cleaves the end fructosyl group of inulin, reducing its DP. Which, as explained above, in turn influences several other characteristics of inulin.³⁸

For oligofructose, the influence of various processing parameters on hydrolysis have also been reported.^{138,139,81,140,141} Hydrolysis of oligofructose also follows pseudo first-order kinetics.^{139,81,140} Little hydrolysis was found up to 60 °C, this changed at 70 °C and above.¹³⁸ Hydrolysis mainly took place at acidic rather than neutral or alkaline conditions, where low molecular weight oligofructose reacted faster than high molecular weight ones.¹³⁹ It was also found that fructose was produced at a higher rate than glucose.¹⁴⁰ Sucrose, containing only a (1 \leftrightarrow 2) linked β -D-glucosyl and β -D-fructosyl group, reacted more slowly than the oligofructose carbohydrates. Combined these results indicate that the terminal β -D-fructosyl-(2 \rightarrow 1)- β -D-fructosyl glycosidic bond is most susceptible to acidic hydrolysis.^{139,81,140} At lower degrees of polymerization this terminal bond is relatively more abundant and they thus have a lower chemical stability. At a pH of around 3, changes in pH of 0.3 units were found to have a large impact on hydrolysis.¹³⁸ At pH 2.7 and a temperature of 90-100 °C nearly complete degradation of oligofructose into monomers was achieved in 30-40 minutes.¹³⁸ At a pH \geq 5, relevant for food applications, no degradation was found regardless of thermal processing (up to 100 °C for 55 minutes).¹⁴²

Inulin and oligofructose thus show similar trends with respect to pH, temperature and molecular weight dependent hydrolysis.⁸¹ The kinetics of the reactions are however different.¹⁴⁰ For higher molecular weight inulins, the rate of hydrolysis is initially low, but increases as hydrolysis progresses.⁸¹ An explanation for this could be the amount of end-chain fructosyl groups. Initially, they are scarce, meaning hydrolysis of mid-chain glycosidic bonds will be more pronounced. Mid-chain hydrolysis in turn increases the amount of more reactive end chain fructosyl groups, resulting in an increase in reaction rate.⁸¹ It was also suggested that the helical structure of inulin, or the lack thereof for oligosaccharides, influences their reaction rate and how those are influenced by temperature.¹⁴⁰

OVERVIEW

Here the physicochemical characteristics of inulin, an oligosaccharide widely used in food and pharma, have been reviewed. The average DP of inulin is often used when describing the physicochemical properties such as solubility and thermal and rheological properties. This generally works well but can potentially also be misleading as the average DP only provides an average and does not provide information on the actual size distribution. Inulin consists of a mixture of polymers of different chain length, its physicochemical properties are to a great extent dependent on the size distribution of this mixture. This means that two different batches of inulin with the same average DP can have different size distributions and therewith different characteristics. Higher DP inulin fractions are less soluble in water, possess higher melting temperatures if crystalline or higher glass transition temperatures if amorphous, are chemically more stable (less sensitive to hydrolysis), form stronger gels and are more viscous when dissolved.

Inulin is used to modify texture or replace fat in food, its DP-sensitive gel forming and viscous behavior make it suitable for that purpose. Additionally, the (2→1) linked fructosyl residues of inulin are not hydrolyzed by the human digestive enzymes, enabling low-calorie replacement of fat. The partially hydrolyzed form of inulin, oligofructose (DP≤10), has this same feature and is more sweet, and is therefore used as a low-calorie sugar replacer. Their indigestibility makes both inulin and oligofructose suitable as dietary fibers. As microbiota in the colon are capable of breaking down inulin, it is also used as a prebiotic and to prepare gels for targeted drug release in the colon.

Inulin's backbone is relatively flexible compared to other polysaccharides, as it does not incorporate the sugar ring. This combined with a relatively high Tg makes inulin a suitable stabilizer of proteins in the dry state for both food and pharma applications. Some specific pharmaceutical applications are its use as a diagnostic agent for kidney function and as an adjuvant for vaccines. Again, the size distribution of the inulin is relevant for these applications. Therefore, regardless of its application both the average DP and the size distribution of inulin should be taken into account. Information on how the molecular weight of inulin and other factors affect its characteristics relevant for its various applications can be found in this chapter.

ACKNOWLEDGEMENTS

This research was jointly financed by Royal FrieslandCampina, the European Union, European Regional Development Fund and The Ministry of Economic Affairs, Agriculture and Innovation, Peaks in the Delta, the Municipality of Groningen, the Provinces of Groningen, Fryslân and Drenthe as well as the Dutch Carbohydrate Competence Center.

REFERENCES

1. Fluckiger, F. A. & Hanbury, D. *Pharmacographia: a history of the principal drugs of vegetable origin met with in Great Britain and British India.* (Macmillan and co., 1879).
2. Livingston, D., Hinch, D. & Heyer, A. in *Recent advances in fructooligosaccharides research* (eds. Norio, S., Noureddine, B. & Shuichi, O.) 661, 181–199 (2007).
3. Kaur, N. & Gupta, A. Applications of inulin and oligofructose in health and nutrition. *J. Biosci.* 27, 703–714 (2002).
4. Van Loo, J. et al. On the presence of inulin and oligofructose as natural ingredients in the western diet. *Crit. Rev. Food Sci. Nutr.* 35, 525–552 (1995).
5. Coussement, P. A. A. Nutritional and health benefits of inulin and oligofructose inulin and oligofructose: safe intakes and legal status 1. *J. Nutr.* 129, 1412–1417 (1999).
6. Carabin, I. G. & Flamm, W. G. Evaluation of safety of inulin and oligofructose as dietary fiber. *Regul. Toxicol. Pharmacol.* 30, 268–282 (1999).
7. Bonnema, A. L., Kolberg, L. W., Thomas, W. & Slavin, J. L. Gastrointestinal tolerance of chicory inulin products. *J. Am. Diet. Assoc.* 110, 865–868 (2010).
8. Closa-Monasterolo, R. et al. Safety and efficacy of inulin and oligofructose supplementation in infant formula: Results from a randomized clinical trial. *Clin. Nutr.* 32, 918–927 (2013).
9. Kruger, C. L. Generally Recognised as Safe (GRAS) Notification for Frutafit®. (Food and Drug Administration, 2002).
10. Orlando, Floreani, Padriani & Palatini. Determination of inulin clearance by bolus intravenous injection in healthy subjects and ascitic patients: equivalence of systemic and renal clearances as glomerular filtration markers. *Br. J. Clin. Pharmacol.* 46, 605–609 (2002).
11. The editors of *Encyclopaedia Britannica*. Inulin clearance. *Encyclopaedia Britannica* (2015). Available at: <http://www.britannica.com/EBchecked/topic/292226/inulin-clearance>. (Accessed: 27th March 2015)
12. Kelly, G. Inulin-type prebiotics--a review: part 1. *Altern. Med. Rev.* 13, 315–329 (2008).
13. Kelly, G. Inulin-type prebiotics: A review (Part 2). *Alternative Medicine Review* 14, 36–55 (2009).
14. Boeckner, L. S., Schnepf, M. I. & Tungland, B. C. Inulin: a review of nutritional and health implications. *Adv. Food Nutr. Res.* 43, 1–63 (2001).
15. Seifert, S. & Watzl, B. Inulin and oligofructose: review of experimental data on immune modulation. *J. Nutr.* 137, 2563S–2567S (2007).
16. Imran, S., Gillis, R. B., Kok, M. S., Harding, S. E. & Adams, G. G. Application and use of Inulin as a tool for the therapeutic drug delivery. *Biotechnol. Genet. Eng. Rev.* 28, 33–45 (2012).
17. Ronkart, S. N. et al. Isolation and identification of inulooligosaccharides resulting from inulin hydrolysis. *Anal. Chim. Acta* 604, 81–87 (2007).
18. Flamm, G., Glinsmann, W., Kritchevsky, D., Prosky, L. & Roberfroid, M. Inulin and oligofructose as dietary fiber: a review of the evidence. *Crit. Rev. Food Sci. Nutr.* 41, 353–362 (2001).
19. Ronkart, S. N. et al. Determination of total water content in inulin using the volumetric Karl Fischer titration. *Talanta* 70, 1006–1010 (2006).
20. Saengthongpinit, W. & Sajjaanantakul, T. Influence of harvest time and storage temperature on characteristics of inulin from Jerusalem artichoke (*Helianthus tuberosus* L.) tubers. *Postharvest Biol. Technol.* 37, 93–100 (2005).
21. IUB-IUPAC Joint Commission on Biochemical Nomenclature (JCBN). Abbreviated Terminology of Oligosaccharide Chains. *J. Biol. Chem.* 257, 3347–3351 (1982).
22. National Center for Biotechnology Information. PubChem Database. Sucrose, Trehalose, Dextran, Amylose (2015). Available at: pubchem.ncbi.nlm.nih.gov. (Accessed: 27th March 2015)
23. Tarantino, L. Generally Recognised as Safe (GRAS) Notification for Hayashibara Trehalose. 1–92 (2000).
24. Council of Europe. in *European Pharmacopoeia 5.0 1970–1971* (Directorate for the quality of medicines & healthcare of the council of Europe, 2005).
25. Potter, A. & Hassid, W. Starch. II. Molecular weights of amyloses and amylopectins from starches of various plant origins. *J. Am. Chem. Soc.* 70, 3774–3777 (1948).
26. Suortti, T., Gorenstein, M. V. & Roger, P. Determination of the molecular mass of amylose. *J. Chromatogr. A* 828, 515–521 (1998).
27. Naessens, M., Cerdobbel, A., Soetaert, W. & Vandamme, E. J. *Leuconostoc* dextranase and dextran: production, properties and applications. *J. Chem. Technol. Biotechnol.* 80, 845–860 (2005).
28. Kim, D., Robyt, J. F., Lee, S.-Y., Lee, J.-H. & Kim, Y.-M. Dextran molecular size and degree of branching as a function of sucrose concentration, pH, and temperature of reaction of *Leuconostoc mesenteroides* B-512FMCM dextranase. *Carbohydr. Res.* 338, 1183–1189 (2003).
29. Klemm, D., Schmauder, H. & Heinze, T. in *Biopolymers Online* 275–287 (Wiley, 2005).

30. Barclay, T., Ginic-Markovic, M., Cooper, P. & Petrovsky, N. Inulin: A versatile polysaccharide with multiple pharmaceutical and food chemical uses. *J. Excipients Food Chem.* 1, 27–50 (2010).
31. Vereyken, I. J. et al. The effect of fructan on the phospholipid organization in the dry state. *Biophys. J.* 85, 3058–3065 (2003).
32. French, A. D. Accessible conformations of the B-D-(2-1)-and-(2-6)-linked D-fructans inulin and levan. *Carbohydr. Res.* 176, 17–29 (1988).
33. French, A. D. & Waterhouse, A. L. in *Science and technology of fructans* (eds. Suzuki, M. & Chatterton, N. J.) 41–82 (CRC Press, Inc., 1993).
34. Tanaka, T., Oi, S. & Yamamoto, T. The molecular structure of low and high molecular weight levans synthesized by levansucrase. *J. Biochem.* 87, 297–303 (1980).
35. Wolff, D. et al. Globular shape of high molar mass inulin revealed by static light scattering and viscometry. *Polymer (Guildf.)* 41, 8009–8016 (2000).
36. Timmermans, J. W. J., van Leeuwen, M. B., Tournois, H., Wit, D. de & Vliegthart, J. F. G. Quantitative analysis of the molecular weight distribution of inulin by means of anion exchange HPLC with pulsed amperometric detection. *J. Carbohydr. Chem.* 13, 881–888 (1994).
37. Blecker, C. S. et al. Characterisation of different inulin samples by DSC: Influence of polymerisation degree on melting temperature. *J. Therm. Anal. Calorim.* 71, 215–224 (2003).
38. Kim, Y., Faqih, M. N. & Wang, S. S. Factors affecting gel formation of inulin. *Carbohydr. Polym.* 46, 135–145 (2001).
39. Franck, A. Technological functionality of inulin and oligofructose. *Br. J. Nutr.* 87, S287 (2002).
40. Apolinário, A. C. et al. Inulin-type fructans: A review on different aspects of biochemical and pharmaceutical technology. *Carbohydr. Polym.* 101, 368–378 (2014).
41. Panchev, I., Delchev, N., Kovacheva, D. & Slavov, A. Physicochemical characteristics of inulins obtained from Jerusalem artichoke (*Helianthus tuberosus* L.). *Eur. Food Res. Technol.* 233, 889–896 (2011).
42. Toneli, J., Mürr, F., Martinelli, P., Dal Fabbro, I. & Park, K. J. Optimization of a physical concentration process for inulin. *J. Food Eng.* 80, 832–838 (2007).
43. Silver, B. S. Inulin fractions. (2002).
44. Silver, B. S. Novel inulin fractions, process for preparing same, and food products containing said inulin fractions. (2000).
45. Blecker, C. S. et al. Novel inulin fractions, preparation and use. (2001).
46. Leite, J., Martinelli, P., Murr, F. & Jin, K. Study of the inulin concentration by physical methods. *Drying B.* 868–875 (2004).
47. Toneli, J., Park, K., Murr, F. & Martinelli, P. Rheological behavior of concentrated inulin solution: Influence of soluble solids concentration and temperature. *J. Texture Stud.* 39, 369–392 (2008).
48. Moerman, F. T., Van Leeuwen, M. B. & Delcour, J. a. Enrichment of higher molecular weight fractions in inulin. *J. Agric. Food Chem.* 52, 3780–3783 (2004).
49. Toneli, J., Park, K., Negreiros, A. & Murr, F. Spray-drying process optimization of chicory root inulin. *Dry. Technol.* 28, 369–379 (2010).
50. Ronkart, S. N. et al. Characterization of the physical state of spray-dried inulin. *Food Biophys.* 2, 83–92 (2007).
51. Ronkart, S. N. et al. Determination of physical changes of inulin related to sorption isotherms: An X-ray diffraction, modulated differential scanning calorimetry and environmental scanning electron microscopy study. *Carbohydr. Polym.* 63, 210–217 (2006).
52. Ronkart, S. N., Paquot, M., Fournies, C., Deroanne, C. & Blecker, C. S. Effect of water uptake on amorphous inulin properties. *Food Hydrocoll.* 23, 922–927 (2009).
53. Ronkart, S. N. et al. Impact of the crystallinity on the physical properties of inulin during water sorption. *Food Biophys.* 4, 49–58 (2008).
54. Ozimek, L. K., Kralj, S., van der Maarel, M. J. E. C. & Dijkhuizen, L. The levansucrase and inulosucrase enzymes of *Lactobacillus reuteri* 121 catalyse processive and non-processive transglycosylation reactions. *Microbiology* 152, 1187–1196 (2006).
55. Wada, T., Sugatani, J., Terada, E., Ohguchi, M. & Miwa, M. Physicochemical characterization and biological effects of inulin enzymatically synthesized from sucrose. *J. Agric. Food Chem.* 53, 1246–1253 (2005).
56. Heyer, A. G. et al. Structure of the enzymatically synthesized fructan inulin. *Carbohydr. Res.* 313, 165–174 (1998).
57. Anwar, M. A. et al. Inulin and levan synthesis by probiotic *Lactobacillus gasseri* strains: characterization of three novel fructansucrase enzymes and their fructan products. *Microbiology* 156, 1264–1274 (2010).
58. Ortiz-Soto, M. E., Olivares-Illana, V. & López-Munguía, A. Biochemical properties of inulosucrase from *Leuconostoc citreum* CW28 used for inulin synthesis. *Biotransformation* 22, 275–281 (2004).
59. Lüscher, M. et al. Inulin synthesis by a combination of purified fructosyltransferases from tubers of

- Helianthus tuberosus*. FEBS Lett. 385, 39–42 (1996).
60. Kurakake, M. et al. Two types of beta-fructofuranosidases from *Aspergillus oryzae* KB. J. Agric. Food Chem. 56, 591–596 (2008).
 61. Silva, M. F. et al. Enzymatic synthesis of fructooligosaccharides by inulinases from *Aspergillus niger* and *Kluyveromyces marxianus* NRRL Y-7571 in aqueous-organic medium. Food Chem. 138, 148–153 (2013).
 62. Beghin-Meji. Actilight® Production process Info. (2015). Available at: <http://www.beghin-meiji.com/actilight/index.php?id=43&menu=2&rub=2&mere=3>. (Accessed: 27th March 2015)
 63. Mutanda, T., Mokoena, M. P., Olaniran, a O., Wilhelmi, B. S. & Whiteley, C. G. Microbial enzymatic production and applications of short-chain fructooligosaccharides and inulooligosaccharides: recent advances and current perspectives. J. Ind. Microbiol. Biotechnol. 41, 893–906 (2014).
 64. Hellwege, E. M., Czaplá, S., Jahnke, A., Willmitzer, L. & Heyer, a G. Transgenic potato (*Solanum tuberosum*) tubers synthesize the full spectrum of inulin molecules naturally occurring in globe artichoke (*Cynara scolymus*) roots. Proc. Natl. Acad. Sci. 97, 8699–8704 (2000).
 65. van Arkel, J. et al. Tailor-made fructan synthesis in plants: a review. Carbohydr. Polym. 93, 48–56 (2013).
 66. Meyer, D., Bayarri, S., Tárrega, A. & Costell, E. Inulin as texture modifier in dairy products. Food Hydrocoll. 25, 1881–1890 (2011).
 67. González-Herrera, S. M. et al. Inulin in food products: prebiotic and functional ingredient. Br. Food J. 117, 371–387 (2015).
 68. Karimi, R., Azizi, M. H., Ghasemlou, M. & Vaziri, M. Application of inulin in cheese as prebiotic, fat replacer and texturizer: A review. Carbohydr. Polym. 119, 85–100 (2015).
 69. Kuntz, M. G. F., Fiates, G. M. R. & Teixeira, E. Characteristics of prebiotic food products containing inulin. Br. Food J. 115, 235–251 (2013).
 70. Rodríguez Furlán, L. T., Lecot, J., Pérez Padilla, A., Campderrós, M. E. & Zaritzky, N. Effect of saccharides on glass transition temperatures of frozen and freeze dried bovine plasma protein. J. Food Eng. 106, 74–79 (2011).
 71. Tunglund, B. C. & Meyer, D. Nondigestible oligo- and polysaccharides (dietary fiber): Their physiology and role in human health and food. Compr. Rev. food Sci. food Saf. 3, 90–109 (2002).
 72. Kolida, S., Tuohy, K. & Gibson, G. R. Prebiotic effects of inulin and oligofructose. Br. J. Nutr. 87, S193 (2002).
 73. Roberfroid, M. B. & Delzenne, N. M. Dietary fructans. Annu. Rev. Nutr. 18, 117–143 (1998).
 74. Hinrichs, W. L. J., Prinsen, M. G. & Frijlink, H. W. Inulin glasses for the stabilization of therapeutic proteins. Int. J. Pharm. 215, 163–174 (2001).
 75. Visser, M. R. et al. Inulin solid dispersion technology to improve the absorption of the BCS Class IV drug TMC240. Eur. J. Pharm. Biopharm. 74, 233–238 (2010).
 76. Stevens, C. V., Meriggi, A. & Booten, K. Chemical modification of inulin, a valuable renewable resource, and its industrial applications. Biomacromolecules 2, 1–16 (2001).
 77. Tonnis, W. F. et al. Size and molecular flexibility of sugars determine the storage stability of freeze-dried proteins. Mol. Pharm. 12, (2015).
 78. Rodríguez Furlán, L. T., Lecot, J., Pérez Padilla, A., Campderrós, M. E. & Zaritzky, N. Stabilizing effect of saccharides on bovine plasma protein: a calorimetric study. Meat Sci. 91, 478–85 (2012).
 79. Honda-Okubo, Y., Saade, F. & Petrovsky, N. Advax™, a polysaccharide adjuvant derived from delta inulin, provides improved influenza vaccine protection through broad-based enhancement of adaptive immune responses. Vaccine 30, 5373–5381 (2012).
 80. de Gennaro, S., Birch, G. G., Parke, S. a. & Stancher, B. Studies on the physicochemical properties of inulin and inulin oligomers. Food Chem. 68, 179–183 (2000).
 81. Blecker, C. S., Fougnes, C., Van Herck, J.-C., Chevalier, J.-P. & Paquot, M. Kinetic study of the acid hydrolysis of various oligofructose samples. J. Agric. Food Chem. 50, 1602–1607 (2002).
 82. Schaller-Povolny, L. A., Smith, D. E. & Labuza, T. P. Effect of water content and molecular weight on the moisture isotherms and glass transition properties of inulin. Int. J. Food Prop. 3, 173–192 (2000).
 83. Hébette, C. L. et al. Complex melting of semi-crystalline chicory (*Cichorium intybus* L.) root inulin. Carbohydr. Res. 310, 65–75 (1998).
 84. Lis, D. G. & Preston, L. A. Methodology for controlling crystal morphology of inulin. (1998).
 85. Ronkart, S. N. et al. Development of gelling properties of inulin by microfluidization. Food Hydrocoll. 24, 318–324 (2010).
 86. Gonzalez-Tomás, L., Coll-Marqués, J. & Costell, E. Viscoelasticity of inulin–starch-based dairy systems. Influence of inulin average chain length. Food Hydrocoll. 22, 1372–1380 (2008).
 87. Bouchard, A. et al. Supercritical fluid drying of carbohydrates: selection of suitable excipients and process conditions. Eur. J. Pharm. Biopharm. 68, 781–794 (2008).
 88. Sigma-Aldrich. Sigma Aldrich. Dextranase product page (2013). Available at: <http://www.sigmaaldrich.com/catalog/product/sigma/d8144>.

89. Azis, B. H., Chin, B., Deacon, M. P., Harding, S. E. & Pavlov, G. M. Size and shape of inulin in dimethyl sulphoxide solution. *Carbohydr. Polym.* 38, 231–234 (1999).
90. Naskar, B., Dan, A., Ghosh, S. & Moulik, S. P. Viscosity and solubility behavior of the polysaccharide inulin in water, water + dimethyl sulfoxide, and water + isopropanol media. *J. Chem. Eng. Data* 55, 2424–2427 (2010).
91. Vereyken, I. J., Albert van Kuik, J., Evers, T. H., Rijken, P. J. & de Kruijff, B. Structural requirements of the fructan-lipid interaction. *Biophys. J.* 84, 3147–3154 (2003).
92. Eigner, W., Abuja, P., Beck, R. & Praznik, W. Physicochemical characterization of inulin and sinistrin. *Carbohydr. Res.* 180, 87–95 (1988).
93. Kitamura, S., Hirano, T. & Takeo, K. Conformation of (2 \rightarrow 1)-beta-D-fructan in aqueous solution. *Int. J. Biol. Macromol.* 16, 313–317 (1994).
94. André, I. et al. Single crystals of inulin. *Int. J. Biol. Macromol.* 18, 195–204 (1996).
95. Marchessault, R. H., Bleha, T., Deslandes, Y. & Revol, J.-F. Conformation and crystalline structure of (2 \rightarrow 1)- β -D-fructofuranan (inulin). *Can. J. Chem.* 58, 2415–2422 (1980).
96. André, I., Mazeau, K. & Tvaroska, I. Molecular and crystal structures of inulin from electron diffraction data. *Macromolecules* 29, 4626–4635 (1996).
97. Oka, M., Ota, N. & Mino, Y. Studies on the conformational aspects of inulin oligomers. *Chem. Pharm. Bull.* 40, 1203–1207 (1992).
98. Liu, J., Waterhouse, A. L. & Chatterton, N. J. Do Inulin Oligomers Adopt a Regular Helical Form in Solution? *J. Carbohydr. Chem.* 13, 859–872 (1994).
99. Naskar, B., Dan, A., Ghosh, S. & Moulik, S. P. Characteristic physicochemical features of the biopolymer inulin in solvent added and depleted states. *Carbohydr. Polym.* 81, 700–706 (2010).
100. Bouchard, A., Hofland, G. W. & Witkamp, G.-J. Properties of Sugar, Polyol, and Polysaccharide Water–Ethanol Solutions. *J. Chem. Eng. Data* 52, 1838–1842 (2007).
101. Bot, A., Erle, U., Vreeker, R. & Agterof, W. G. M. Influence of crystallisation conditions on the large deformation rheology of inulin gels. *Food Hydrocoll.* 18, 547–556 (2004).
102. Cooper, P. D. & Carter, M. Anti-complementary action of polymorphic ‘solubility forms’ of particulate inulin. *Mol. Immunol.* 23, 895–901 (1986).
103. Cooper, P. D. & Petrovsky, N. Delta inulin: a novel, immunologically active, stable packing structure comprising -D-[2 \rightarrow 1] poly(fructo-furanosyl)-D-glucose polymers. *Glycobiology* 21, 595–606 (2011).
104. Cooper, P. D., Barclay, T. G., Ginic-Markovic, M. & Petrovsky, N. The polysaccharide inulin is characterized by an extensive series of periodic isoforms with varying biological actions. *Glycobiology* 23, 1164–1174 (2013).
105. Cooper, P. D., Barclay, T. G., Ginic-Markovic, M., Gerson, A. R. & Petrovsky, N. Inulin isoforms differ by repeated additions of one crystal unit cell. *Carbohydr. Polym.* 103, 392–397 (2014).
106. Ronkart, S. N., Deroanne, C., Paquot, M., Fougnes, C. & Blecker, C. S. Impact of the crystallisation pathway of inulin on its mono-hydrate to hemi-hydrate thermal transition. *Food Chem.* 119, 317–322 (2010).
107. Cooper, P. D. et al. Inulin crystal initiation via a glucose-fructose cross-link of adjacent polymer chains: Atomic force microscopy and static molecular modelling. *Carbohydr. Polym.* 117, 964–972 (2015).
108. Glibowski, P. Effect of thermal and mechanical factors on rheological properties of high performance inulin gels and spreads. *J. Food Eng.* 99, 106–113 (2010).
109. Dan, A., Ghosh, S. & Moulik, S. P. Physicochemical studies on the biopolymer inulin: a critical evaluation of its self-aggregation, aggregate-morphology, interaction with water, and thermal stability. *Biopolymers* 91, 687–699 (2009).
110. Phelps, C. F. The physical properties of inulin solutions. *Biochem. J.* 95, 41–7 (1965).
111. van Duynhoven, J. P. M., Kulik, A. S., Jonker, H. R. A. & Haverkamp, J. Solid-like components in carbohydrate gels probed by NMR spectroscopy. *Food Chem.* 40, 211–219 (1999).
112. Kim, Y. & Wang, S. S. Kinetic study of thermally induced inulin gel. *J. Food Sci.* 66, 991–997 (2001).
113. Chiavaro, E., Vittadini, E. & Corradini, C. Physicochemical characterization and stability of inulin gels. *Eur. Food Res. Technol.* 225, 85–94 (2006).
114. Szczesniak, A. Classification of textural characteristics. *J. Food Sci.* 28, 385–389 (1963).
115. Glibowski, P., Pikus, S., Jurek, J. & Kotowoda, M. Factors affecting inulin crystallization after its complete dissolution. *Carbohydr. Polym.* 110, 107–112 (2014).
116. Alvarez-Sabatel, S., Marañón, I. M. De & Arboleya, J.-C. Impact of high pressure homogenisation (HPH) on inulin gelling properties, stability and development during storage. *Food Hydrocoll.* 44, 333–344 (2015).
117. Tseng, Y.-C., Xiong, Y. L. & Boatright, W. L. Effects of inulin/oligofructose on the thermal stability and acid-induced gelation of soy proteins. *J. Food Sci.* 73, E44–50 (2008).
118. Soukoulis, C., Lebesi, D. & Tzia, C. Enrichment of ice cream with dietary fibre: Effects on rheological properties, ice crystallisation and glass transition phenomena. *Food Chem.* 115, 665–671 (2009).

119. Pitarresi, G., Giacomazza, D., Triolo, D., Giammona, G. & San Biagio, P. L. Rheological characterization and release properties of inulin-based hydrogels. *Carbohydr. Polym.* 88, 1033–1040 (2012).
120. Castelli, F. et al. Differential scanning calorimetry study on drug release from an inulin-based hydrogel and its interaction with a biomembrane model: pH and loading effect. *Eur. J. Pharm. Sci.* 35, 76–85 (2008).
121. Fares, M. M., Salem, M. S. & Khanfar, M. Inulin and poly(acrylic acid) grafted inulin for dissolution enhancement and preliminary controlled release of poorly water-soluble irbesartan drug. *Int. J. Pharm.* 410, 206–211 (2011).
122. Van den Mooter, G., Vervoort, L. & Kinget, R. Characterization of methacrylated inulin hydrogels designed for colon targeting: in vitro release of BSA. *Pharm. Res.* 20, 303–307 (2003).
123. Vervoort, L. et al. Inulin hydrogels as carriers for colonic drug targeting: I. Synthesis and characterization of methacrylated inulin and hydrogel formation. *Pharm. Res.* 14, 1730–1737 (1997).
124. Vervoort, L. et al. Inulin hydrogels as carriers for colonic drug targeting. Rheological characterization of the hydrogel formation and the hydrogel network. *J. Pharm. Sci.* 88, 209–14 (1999).
125. Maris, B. et al. Synthesis and characterisation of inulin-azo hydrogels designed for colon targeting. *Int. J. Pharm.* 213, 143–152 (2001).
126. Cavalcanti, O. A., Van den Mooter, G., Caramico-Soares, I. & Kinget, R. Polysaccharides as excipients for colon-specific coatings. Permeability and swelling properties of casted films. *Drug Dev. Ind. Pharm.* 28, 157–64 (2002).
127. Tripodo, G., Pitarresi, G., Palumbo, F. S., Craparo, E. F. & Giammona, G. UV-photocrosslinking of inulin derivatives to produce hydrogels for drug delivery application. *Macromol. Biosci.* 5, 1074–1084 (2005).
128. Sahiner, N., Sagbas, S., Yoshida, H. & Lyon, L. A. Synthesis and properties of inulin based microgels. *Colloids Interface Sci. Commun.* 2, 15–18 (2014).
129. Fox, T. G. & Flory, P. J. Second-order transition temperatures and related properties of polystyrene. I. Influence of molecular weight. *J. Appl. Phys.* 21, 581–591 (1950).
130. Kawai, K., Fukami, K., Thanatuksorn, P., Viriyarattanasak, C. & Kajiwara, K. Effects of moisture content, molecular weight, and crystallinity on the glass transition temperature of inulin. *Carbohydr. Polym.* 83, 934–939 (2011).
131. Velikov, V., Borick, S. & Angell, C. a. The glass transition of water, based on hyperquenching experiments. *Science (80-.)*. 294, 2335–2338 (2001).
132. Giovambattista, N., Angell, C. A., Sciortino, F. & Stanley, H. E. The glass transition temperature of water: A simulation study. *Phys. Rev. Lett.* 93, 47801 (2004).
133. Gordon, M. & Taylor, J. Ideal copolymers and the second-order transitions of synthetic rubbers. i. non-crystalline copolymers. *J. Appl. Chem.* 2, 493–500 (1952).
134. Zimeri, J. E. & Kokini, J. L. The effect of moisture content on the crystallinity and glass transition temperature of inulin. *Carbohydr. Polym.* 48, 1998–2003 (2002).
135. Flory, P. & Vrij, A. Melting points of linear-chain homologs. The normal paraffin hydrocarbons. *J. Am. Chem. Soc.* 85, 3548–3553 (1963).
136. BeMiller, J., Steinheimer, T. & Allen, E. Alkaline degradation of inulin and its structural implications. *Clin. Chem.* 13, 261–269 (1967).
137. Martins, S. I. F. S., Jongen, W. M. F. & Boekel, M. A. J. S. Van. A review of Maillard reaction in food and implications to kinetic modelling. *Trends Food Sci. Technol.* 11, 364–373 (2001).
138. Matusek, A., Merész, P., Le, T. K. D. & Örsi, F. Effect of temperature and pH on the degradation of fructooligosaccharides. *Eur. Food Res. Technol.* 228, 355–365 (2008).
139. L'homme, C., Arbelot, M., Puigserver, A. & Biagini, A. Kinetics of hydrolysis of fructooligosaccharides in mineral-buffered aqueous solutions: influence of pH and temperature. *J. Agric. Food Chem.* 51, 224–228 (2003).
140. Barclay, T., Ginic-Markovic, M., Johnston, M. R., Cooper, P. D. & Petrovsky, N. Analysis of the hydrolysis of inulin using real time ¹H NMR spectroscopy. *Carbohydr. Res.* 352, 117–125 (2012).
141. Vega, R. & Zuniga-Hansen, M. E. The effect of processing conditions on the stability of fructooligosaccharides in acidic food products. *Food Chem.* 173, 784–789 (2015).
142. Glibowski, P. & Bukowska, A. The effect of pH, temperature and heating time on inulin chemical stability. *Acta Sci. Pol. Technol. Aliment.* 10, 189–196 (2011).

