

University of Groningen

Electronic transport properties of pentacene single crystals upon exposure to air

Jurchescu, O. D.; Baas, J.; Palstra, T. T. M.

Published in:
 Applied Physics Letters

DOI:
[10.1063/1.2001130](https://doi.org/10.1063/1.2001130)

IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.

Document Version
 Publisher's PDF, also known as Version of record

Publication date:
 2005

[Link to publication in University of Groningen/UMCG research database](#)

Citation for published version (APA):

Jurchescu, O. D., Baas, J., & Palstra, T. T. M. (2005). Electronic transport properties of pentacene single crystals upon exposure to air. *Applied Physics Letters*, 87(5), Article 052102.
<https://doi.org/10.1063/1.2001130>

Copyright

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

Take-down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.

Electronic transport properties of pentacene single crystals upon exposure to air

Oana D. Jurchescu, Jacob Baas, and Thomas T. M. Palstra^{a)}

Solid State Chemistry Laboratory, Materials Science Centre, University of Groningen, Nijenborgh 4, 9747 AG Groningen, The Netherlands

(Received 27 January 2005; accepted 9 June 2005; published online 26 July 2005)

We report the effect of air exposure on the electronic properties of pentacene single crystals. Air can diffuse reversibly in and out of the crystals and influences the physical properties. We discern two competing mechanisms that modulate the electronic transport. The presence of oxygen increases the hole conduction, as *in dark* four O₂ molecules introduce one charge carrier. This effect is enhanced by the presence of visible light. Contrarily, water, present in ambient air, is incorporated in the crystal lattice and forms trapping sites for injected charges. © 2005 American Institute of Physics. [DOI: 10.1063/1.2001130]

Pentacene is a good material for electronic devices like field effect transistors.^{1–8} However, the results obtained by different research groups are not always consistent. This can be attributed in part to the fact that the performance of the devices depends critically on the environmental conditions.^{9–11}

We report the electronic properties of pentacene single crystals under controlled conditions of pressure, gas composition, illumination, and in time. We provide experimental evidence that the influence of air on the charge carrier conduction consists of two separate, distinguishable contributions. Air diffuses into pentacene and can be completely removed by reevacuation. Thus, no irreversible chemical reactions, like oxidation of pentacene to pentacenequinone, can be detected during the diffusion process. We demonstrate that oxygen absorption is responsible for an increase in the conductivity, and its effect is enhanced by the presence of visible light. In contrast, water present in ambient air will form trapping sites for the injected charges. This will reduce the number of free charge carriers, and thus the value of the conductivity. These opposite effects may account for the contradicting reports on the influence of ambient conditions.

Pentacene single crystals with a high degree of purity were grown using the vapor transport technique.¹² The growth was preceded by the purification of the starting material using a two-step vacuum sublimation process under a temperature gradient described elsewhere.⁸ We performed thermogravimetric analysis (TGA) on pentacene single crystals at room temperature to determine the changes in mass. The increase in weight at normal pressure in the presence of different gas flows (air, O₂, N₂, and Ar) were measured using a SDT 2960 from Thermal Analysis Instruments.

The crystals are platelets with dimensions of $\sim 3 \times 3$ mm in plane and thickness of 15–20 μm . Silver epoxy stripe contacts were painted on the crystal, with a distance of 3 mm. The electrical measurements were performed in a home built micromanipulator probe station, connected to a turbopump and to gas supplies. The system is equipped with a glass window for optical inspection. This window is covered for the experiments performed *in dark* (Fig. 2). Other-

wise, the samples are exposed to ambient fluorescent light (Fig. 3), with no additional illumination. A Hewlett Packard 4155B Semiconductor Parameters Analyzer was used to perform electrical measurements. All measurements were performed at room temperature.

Figure 1 shows the evolution in time of the current density J versus applied voltage V characteristics for single crystal pentacene *in dark*, after venting the system with dry and ambient air, respectively. We associate the behavior at low bias with Ohmic behavior: $J \propto V^x$ with $x=1$. The observed values of x range from 0.7 to 1.3 for different samples, which we relate to the quality of the contacts. In this regime, no marked changes in the conductivity are induced by the presence of oxygen or water vapor. However, the space-charge-limited current regime SCLC ($J \propto V^2$) is influenced by exposure to air. Here, J increases upon exposure to dry air, whereas J decreases upon exposure to ambient air. We interpret this behavior that the induced carriers are located in shallow trapped states and are only released beyond a critical field. The quantitative analysis of the transport changes, introduced by absorbing air, are performed in the SCLC regime ($V=100$ V). In dry air, the number of holes introduced

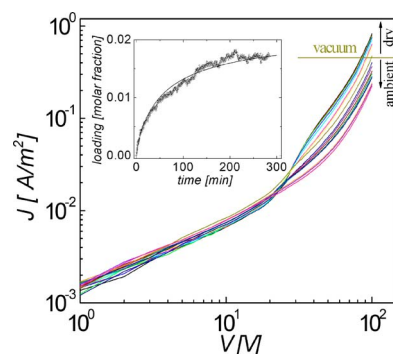


FIG. 1. Current density J vs. applied voltage V for pentacene single crystal at room temperature in vacuum and after exposure to dry air (increase in J) and ambient air (decrease in J). The different colors of the curves represent different exposure times. In pure air: (–250 min), (–200 min), (–150 min), (–100 min), (–50 min), (–10 min), (–0 min), (–in vacuum). In ambient air: (–0 min), (–10 min), (–20 min), (–30 min), (–50 min), (–100 min), (–150 min), (–200 min), (–250 min). The inset represents the evolution in time of the molar fraction of air in pentacene upon exposure of single crystals to dry air at room temperature and the fit with a 1D diffusion model.

^{a)} Author to whom correspondence should be addressed; electronic mail: t.t.m.palstra@rug.nl

by the O₂ molecules increases in time, leading to an increase in the charge carrier density. The system will achieve the SCLC regime at smaller bias voltage.

In the inset of Fig. 1 we plot the weight increase of pentacene single crystals upon exposure to 5N dry air (<17 ppm water vapor), at room temperature and atmospheric pressure, expressed as a molar fraction of air in pentacene. The mass of the accumulated air in the crystal structure of pentacene was calculated assuming that the change in mass is caused only by absorption of gases. This assumption is supported by the observation that the process is completely reversible. The same trend is observed for the measurements performed in pure O₂, N₂, and Ar. The time constants are determined by the size and shape of both crystals and diffusing molecules. As the diffusion coefficients have similar values, we conclude that there is no selectivity with respect to any of the gases. The saturation values are within experimental accuracy the same for the different gases: 2.0% ± 0.3%.

We used Fick's second law to model the diffusion of gases into pentacene single crystals. We solve this equation for the one-dimensional case, constant diffusion coefficient D , and an inexhaustible source. The total quantity of gas molecules in the pentacene crystal is obtained by integrating this solution over the length of the diffusion profile. The result is normalized and expressed in molar fraction of gas molecules in pentacene. An extra term needs to be added in the solution (N_{start}). This term reflects the fact that the measurement starts at $t=0$ with a quantity of gas that was accumulated in crystal during venting to atmospheric pressure and subsequent handling. The equation that models the diffusion of gases in pentacene is thus:

$$N(t) = N_{\text{start}} + N_{\text{source}} \left\{ d \left[1 - \operatorname{erf} \left(\frac{d}{2\sqrt{Dt}} \right) \right] + \frac{2}{\sqrt{\pi}} \cdot \sqrt{Dt} \cdot \left[1 - \exp \left(-\frac{d^2}{4Dt} \right) \right] \right\}, \quad (1)$$

where $N(t)$ is the molar fraction of gas at time t , N_{source} is imposed by the gas flow, d is the length of the crystal in the direction in which the 1D diffusion occurs, D is the diffusion coefficient, and N_{start} is the value of the molar fraction accumulated before the TGA measurement. For the case of dry air (inset Fig. 1), fitting the diffusion curve yields $d = 17.5 \mu\text{m}$, $D = 1.8 \times 10^{-10} \text{ cm}^2/\text{s}$ and $N_{\text{start}} = -1.37 \times 10^{-3}$ molecules air/molecules pentacene. Our results show that the diffusion length is similar to the thickness of the crystal. Therefore, the diffusion proceeds via the largest surface area, perpendicular to the layers. This suggests that the oxygen molecules may not accumulate between the van der Waals bonded layers, but within the layers.

We investigate the influence of the absorbed gas molecules on the changes in the electrical current. Prior to the experiments, the samples were outgassed in vacuum ($p = 5 \times 10^{-7}$ mbar) in the measurement chamber for at least 100 min. The measurements can be reproduced after reevacuation, as the gases diffuse reversibly in and out of the crystal. In order to study the influence of environmental conditions on the electrical properties, the pentacene single crystals were exposed to both 5N dry air and ambient air, using a leak-valve connected to the measurement chamber. For the experiments performed *in dark*, we measured both while outgassing and venting the chamber to ensure that the changes

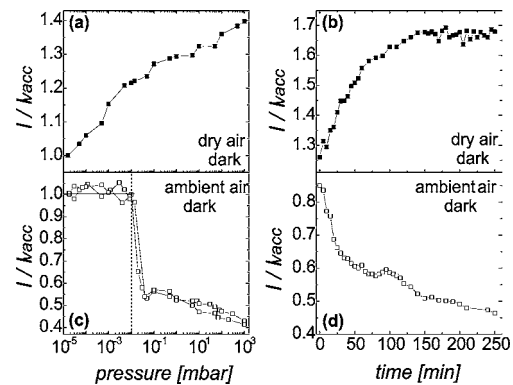


FIG. 2. Pressure (a), (c) and time (b), (d) dependence of the current at fixed bias voltage for single crystal pentacene in dark.

originate from diffusion and not from charging. The evolution of the electrical properties in time was recorded immediately after venting the system to atmospheric pressure. The initial time, $t=0$, is taken when pressure equals atmospheric pressure.

The effect of oxygen exposure in dark is studied when venting with dry air Figs. 2(a) and 2(b). As the pressure increases [Fig. 2(a)], oxygen will diffuse into the crystal, and the conductivity increases. The I - V curves are measured immediately after the desired pressure is reached. Once the system is at atmospheric pressure, the current continues to increase [Fig. 2(b)] because the diffusion still continues. A comparison of the inset in Fig. 1, with Fig 2(b) reveals a remarkable consistency. The time evolution of the electrical current mirrors that of the oxygen absorption. When venting with ambient air, both water vapor, and oxygen are introduced into the chamber [Figs. 2(c) and 2(d)]. We noticed that in ambient air, the effect of oxygen exposure is counteracted by the exposure to water. Analyzing the magnitude of the induced changes in the current by combining oxygen and water, one can distinguish two pressure regimes [Fig. 2(c)]. At low pressure ($p < 10^{-2}$ mbar), the conduction is independent of air pressure. This leads us to conclude that the two effects are opposite and of the same magnitude. At $p = 10^{-2}$ mbar, a sudden drop in the current is observed. Apparently, for $p > 10^{-2}$ mbar the introduction of scattering sites exceeds the creation of holes, and this has a major effect on the conduction. This is reflected also in the results at atmospheric pressure, where diffusion of dry air causes a current increase of 25% [Fig. 2(b)], whereas ambient air diffusion cause a drop of 45% [Fig. 2(d)].

Figure 3 shows the evolution of the current under the same conditions, but now in the presence of *light*. The effect of oxygen diffusion is stronger than *in dark* [Figs. 3(a) and 3(b)]. This is reflected in the increase of the current, which is a factor 2.4 larger in dry air than in ambient air. As the effect of water is independent of the presence of *light*, the total influence of ambient air on the crystal properties will be different in the presence of *light*. Consistent with the measurements *in dark*, we find two pressure regimes. At low pressure ($p < 10^{-2}$ mbar), the oxygen doping is the dominant factor of the conduction mechanism. At $p = 10^{-2}$ mbar, the effect of oxygen is decreased, and therefore a change in slope is observed [Fig. 3(c)]. However, the presence of oxygen remains the most important factor, as the value of the current increases with pressure. After venting with ambient air, the doping caused by oxygen, activated by illumination,

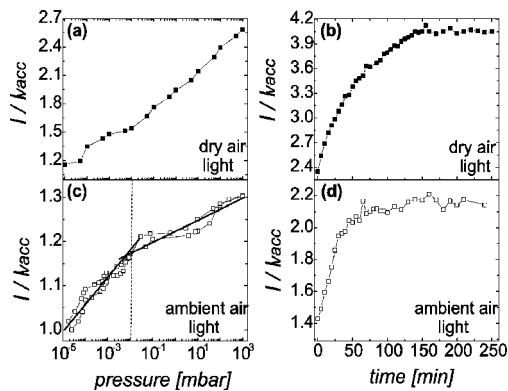


FIG. 3. Dependence of the current at fixed bias voltage for single crystal pentacene of pressure (a), (c) and time at normal pressure (b), (d) exposed ambient fluorescent light.

gives a stronger effect than the trapping of charges by water.

We relate the changes that we observe in the electrical properties to the diffusion of gases into the crystal. Our model includes two competing mechanisms associated with the two different chemical species that influence the conduction, affected by external factors such as light. On the one hand, water absorbed by exposure to ambient air,¹³ will create new trapping sites for the charges that are injected from the electrodes.¹⁴ This will decrease the value of the electrical conductivity. This effect is independent of the exposure to *light*. The polar nature of the H₂O molecules causes interactions with the injected charges and increases the energetic disorder.¹⁵ This will lead to a decrease of the conduction. Oxygen present in air will be incorporated in the crystal structure, as shown in the inset in Fig. 1. Because of its electronegativity, it will attract electrons from the pentacene molecules and this process will generate holes. The density of charge carriers responsible for the conduction will thus increase, and accordingly the value of the current will increase. This process is enhanced by the presence of *light*. The measurements performed in pure N₂ and Ar under identical conditions show insignificant changes in the electrical properties, despite a similar amount of absorption.

The value of the hole current is affected by the number of gas molecules present in the crystal and thus varies in time: $J_p(t) = e\mu_p p(t)E$, where e is the elementary charge and μ_p is the mobility of holes in pentacene. The term $p(t)$ is the density of charge carriers and consists of several terms: $p(t) = p_{inj} + p_{dop} - p_{traps}$. Here p_{inj} represents the hole density injected from the contacts, and p_{dop} is the hole density induced by exposure to oxygen, which is a fraction of the number of air molecules absorbed in the solid, $p_{dop} = 0.2 \cdot \eta_{\text{oxygen}} \cdot N(t)$. The oxygen efficiency η_{oxygen} is thus defined as the inverse of the number of oxygen molecules required to generate one hole. The term $p_{traps} = p_{def} + p_{imp} + p_{water}$ is the density of traps in the band gap. In vacuum a fraction of the injected charges are trapped by crystal defects, p_{def} , and impurities, p_{imp} . In ambient air, an extra term is added in the trapping sites due to the presence of water molecules, $p_{water}(t) = \beta N(t)$, which is a fraction of total number of the air molecules $N(t)$ accumulated in the crystal. Combining the measurements performed in pure air [Figs. 2(b) and 3(b)], with $N(t)$ taken from Fig. 1(inset), we can determine

the oxygen efficiency η_{oxygen} . This number is constant and independent of time with $\eta_{\text{oxygen}} \approx 0.25$ in dark and $\eta_{\text{oxygen}} \approx 0.5$ in light. This means that the efficiency of the oxygen exposure induced doping is independent of oxygen loading and it is increased by light exposure. Roughly two O₂ molecules are needed *in light* to create one hole, compared with four molecules *in dark*.

In ambient air, the number of trapping sites is proportional to the number of water molecules that diffuse into the crystal. We introduce the ratio: $\Theta_{\text{water}} = p_{inj} - p_{water} / p_{inj}$ that quantifies the fraction of untrapped charge carriers: $\Theta_{\text{water}} = 1$ in vacuum. After exposure to ambient air, the value of Θ_{water} is reduced. Θ_{water} is calculated by subtracting Fig. 2(b) and 3(b) from Fig. 2(d) and 3(d), using appropriate geometrical factors. The effects of water *in dark* and *light* have similar magnitudes, and they follow the diffusion of water, introduced from ambient air.

In conclusion, we have investigated the intercalation of gases in pentacene single crystals¹⁶ and its effect on the electronic properties. We differentiate between the exposure to oxygen and water. Absorbed oxygen enhances the conduction by introducing holes near the valance band. Absorbed water molecules create new defect states, which trap the injected charges. This insight in the relationship between the macroscopic diffusion of gas in organic conductors and the effect on the physical properties may lead to an improved control of the device performance.

The authors would like to thank P. Rudolf, N. Koch, R. Broer, P. de Boeij, and P. Blom for stimulating discussions. This work is part of the MSC^{plus} Program.

¹V. Y. Butko, X. Chi, D. V. Lang, and A. P. Ramirez, Appl. Phys. Lett. **83**, 4773 (2003).

²J. Takeya, C. Goldmann, S. Haas, K. P. Pernstich, B. Ketterer, and B. Batlogg, J. Appl. Phys. **94**, 5800 (2003).

³C. Goldmann, S. Haas, C. Krellner, K. P. Pernstich, D. J. Gundlach, and B. Batlogg, J. Appl. Phys. **96**, 2080 (2003).

⁴G. H. Gelinck, H. E. A. Huijtema, E. van Veenendaal, E. Cantatore, L. Schrijnemakers, J. B. P. H. van der Putten, T. C. T. Geuns, M. Beenhakkers, J. B. Giesbers, B.-H. Huisman, E. J. Meijer, E. M. Benito, F. J. Touwslager, A. W. Marsman, B. J. E. van Rens, and D. M. de Leeuw, Nat. Mater. **3**, 106 (2004).

⁵T. Yasuda, T. Goto, K. Fujita, and T. Tsutsui, Appl. Phys. Lett. **85**, 2098 (2004).

⁶T. Minari, T. Nemoto, and S. Isoda, J. Appl. Phys. **96**, 769 (2004).

⁷C. C. Mattheus, A. B. Dros, J. Baas, G. T. Oostergetel, A. Meetsma, J. L. de Boer, and T. T. M. Palstra, Synth. Met. **138**, 475 (2003).

⁸O. D. Jurchescu, J. Baas, and T. T. M. Palstra, Appl. Phys. Lett. **84**, 3061 (2004).

⁹B. Crone, A. Dodabalapur, A. Gelperin, L. Torsi, H. E. Katz, A. J. Lovinger, and Z. Bao, Appl. Phys. Lett. **78**, 2229 (2001).

¹⁰A. Assadi, G. Gustafsson, M. Willander, C. Svensson, and O. Inganäs, Synth. Met. **37**, 123 (1990).

¹¹L. Tosi, A. Dodabalapur, N. Cioffi, L. Sabbatini, and P. G. Zambonin, Sens. Actuators B **77**, 7 (2001).

¹²A. Laudise, C. Kloc, P. Simpkins, and T. Siegrist, J. Cryst. Growth **187**, 449 (1998).

¹³Y. Qiu, Y. Hu, G. Dong, L. Wang, J. Xie, and Y. Ma, Appl. Phys. Lett. **83**, 1644 (2003).

¹⁴Z. T. Zhu, J. T. Mason, R. Dieckmann, and G. G. Malliaras, Appl. Phys. Lett. **81**, 4643 (2002).

¹⁵D. H. Dunlap, P. E. Parris, and V. M. Kenkre, Phys. Rev. Lett. **77**, 542 (1996).

¹⁶A. Vollmer, O. D. Jurchescu, I. Arfaoui, T. T. M. Palstra, P. Rudolf, J. Niemax, J. Pflaum, I. Salzmann, J. P. Rabe, and N. Koch (unpublished).