

University of Groningen

## In Silico Design of Robust Bolalipid Membranes

Bulacu, Monica; Periole, Xavier; Marrink, Siewert J.; Périole, Xavier

*Published in:*  
Biomacromolecules

*DOI:*  
[10.1021/bm201454J](https://doi.org/10.1021/bm201454J)

**IMPORTANT NOTE: You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.**

*Document Version*  
Publisher's PDF, also known as Version of record

*Publication date:*  
2012

[Link to publication in University of Groningen/UMCG research database](#)

*Citation for published version (APA):*

Bulacu, M., Periole, X., Marrink, S. J., & Périole, X. (2012). In Silico Design of Robust Bolalipid Membranes. *Biomacromolecules*, 13(1), 196-205. <https://doi.org/10.1021/bm201454J>

**Copyright**

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

**Take-down policy**

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

*Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.*

# Supporting information for: *In-silico* design of robust bolalipid membranes

Monica Bulacu, Xavier Périole, and Siewert J. Marrink\*

*Groningen Biomolecular Sciences and Biotechnology Institute and Zernike Institute for Advanced  
Materials, University of Groningen, Nijenborgh 4, 9747 AG Groningen, The Netherlands*

E-mail: s.j.marrink@rug.nl

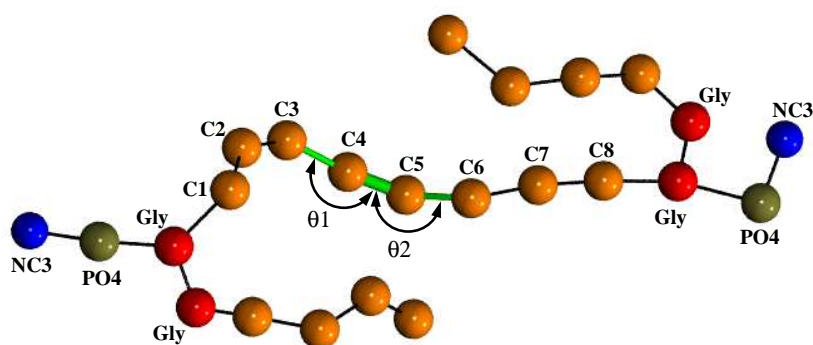


Figure 1: The coarse-grained model of a bola lipid (acyclic). Orange represents the methylene units, red the glycerol, blue the choline and tan the phosphate. The thick green bond is the covalent bond between the last beads from the tails of two DPPC lipids. Two bending potentials acting on the angles  $\theta_1$  and  $\theta_2$  control the linker stiffness (with equilibrium angle  $\theta = 180^\circ$  and  $K = 25 \text{ kJ mol}^{-1}$ ). Three cases are considered for the linker: stiff — bending potential on both angles, semi-flexible — only  $\theta_1$  is controlled, and flexible — both  $\theta_1$  and  $\theta_2$  are free.

---

\*To whom correspondence should be addressed

Table 1: Structural and dynamic properties of the bolalipid membranes: average fraction of trans conformers, area per lipid head group  $A$ , membrane thickness  $d_{pp}$ , and lipid lateral diffusion rate  $D$ . The (a) superscript refers to membranes in the gel phase, the (b) superscript to pre-assembled membranes with exclusively trans-conformations. The errors reported for  $A$  and  $d_{pp}$  are standard errors obtained by dividing each trajectory in independent blocks of 50 ns. The standard errors in  $D$  were obtained from the deviation between the five independent simulations for each type of system. Likewise, the standard error of the trans fraction is estimated around 2 – 3%.

system	linker type	trans [%]	T [K]	$A$ [nm <sup>2</sup> ]	$d_{pp}$ [nm]	$D$ [ $10^{-7} cm^2/s$ ]
DPPC	-	-	323	$0.633 \pm 0.001$	$4.13 \pm 0.05$	$9.2 \pm 0.2$
	-	-	363	$0.698 \pm 0.001$	$3.94 \pm 0.07$	$17.1 \pm 0.2$
acyclic di-DPPC	stiff	90	323	$0.600 \pm 0.001$	$4.25 \pm 0.05$	$1.8 \pm 0.1$
	stiff <sup>b</sup>	100	323	$0.593 \pm 0.001$	$4.28 \pm 0.04$	$2.0 \pm 0.3$
	semi-flexible	60	323	$0.616 \pm 0.002$	$4.19 \pm 0.09$	$1.7 \pm 0.1$
	flexible	40	323	$0.618 \pm 0.002$	$4.16 \pm 0.09$	$2.3 \pm 0.4$
cyclic di-DPPC	stiff <sup>a</sup>	96	363	$0.568 \pm 0.007$	$4.45 \pm 0.11$	$0.2 \pm 0.1$
	stiff <sup>a,b</sup>	100	363	$0.500 \pm 0.004$	$4.60 \pm 0.03$	-
	semi-flexible	70	363	$0.632 \pm 0.001$	$4.15 \pm 0.11$	$2.7 \pm 0.2$
	semi-flexible <sup>a,b</sup>	100	363	$0.578 \pm 0.003$	$4.38 \pm 0.08$	-
	flexible	40	323	$0.603 \pm 0.001$	$4.26 \pm 0.10$	$0.9 \pm 0.2$